

# Nano-Diamond Obtained from Adipic Acid at Ultra-High Pressures

I.Konyashin<sup>1,2\*</sup>, D.J. Frost<sup>3</sup>, A. Crossley<sup>4</sup>, K. Jurkschat<sup>4</sup>, C. Johnston<sup>4</sup>, K. Armstrong<sup>3</sup>

<sup>1</sup> Element Six GmbH, Burghaun, Germany

<sup>2</sup> National University of Science and Technology “MISIS”, Moscow Russia

<sup>3</sup> University of Bayreuth, Bayreuth, Germany

<sup>4</sup> Department of Materials, Oxford University, Begbroke Science Park, Begbroke Hill, Oxford, Great Britain

\*Corresponding author, email: [igor.konyashin@e6.com](mailto:igor.konyashin@e6.com)

## Abstract

Adipic acid was used in this work as a carbon-containing precursor for the HPHT synthesis of a carbon sample containing nano-diamond. The carbon sample consists of lamellar diamond nano-grains of about 30 to 50 nm embedded in an amorphous or poorly crystallized carbon matrix. The carbon sample comprises mainly  $sp^2$ -hybridized carbon in form of graphite or amorphous carbon.

## 1.Introduction

Traditionally, synthetic diamond grits and diamond-based materials, polycrystalline diamond containing a Co-based binder (PCD), are manufactured by high-pressure high-temperature (HPHT) processes at pressures above 5 GPa with the aid of Fe-group metals having a catalytic effect on the transformation of  $sp^2$ -hybridized carbon into diamond.

Another route for the diamond fabrication is based on the direct conversion of carbon-based precursors, usually graphite or amorphous carbon, at pressures of above nearly 12 GPa [1, 2]. In the beginning of the 2000's it was shown that it is possible to fabricate nano-diamond with a mean grain size of below 100 nm by the direct conversion of graphite into pure polycrystalline diamond (see e.g. refs. [3, 4]). The nano-diamond obtained in such a way is characterized by superior hardness, cutting performance and other properties [5 – 8]. Different carbon-based  $sp^2$ -hybridized precursors were employed for the fabrication of nano-diamond by use of the direct conversion process [3, 9 -11] and it was established that their behavior is different with respect to the nano-diamond formation.

It can be expected that the employment of organic precursors could facilitate the formation of nano-diamond at high temperatures and ultra-high pressures, especially when the precursors contain significant amounts of oxygen. Oxygen is thought to react with hydrogen during the decomposition of such organic precursors resulting in the formation of high-pressure water vapor in a capsule employed for HPHT experiments at high temperatures and ultra-high pressures. As a result, the formation of nano-diamond can be enhanced and also metastable forms of carbon might be obtained.

The major objective of this work was to evaluate the possibility of the nano-diamond formation by use of an organic oxygen-containing precursor at ultra-high pressures.

## **2.Experimental details.**

Adipic acid with the formula  $(\text{CH}_2)_4(\text{COOH})_2$ , which is a powder at room temperature, was used in this work as a precursor for the direct conversion into a carbon sample containing nano-diamond grains. The sample was compressed using a custom-built 5000-ton multi-anvil press at a temperature of 1235°C and pressure of 14 GPa for 1 h. The adipic acid powder was placed inside a thin graphite sleeve and welded into a 2 mm diameter gold capsule. A 0.025 mm thick piece of molybdenum foil was placed at the bottom of the capsule to fix the oxygen fugacity. The capsule was carefully compressed to produce a cylinder 3.5 mm long and placed inside a cylindrical sleeve made of hexagonal boron nitride (h-BN). The capsule and sleeve was placed at the center of a  $\text{LaCrO}_3$  (Sr-doped) cylindrical heater. Space below the capsule was filled with an MgO cylinder, while from above a W3%Re-W25%Re (type d) thermocouple inside a 4-bore alumina tube was inserted through a further MgO sleeve. The furnace was surrounded by a  $\text{ZrO}_2$  insulator. The entire assembly was placed into a 6.8 mm diameter hole bored into an 18 mm edge length MgO ( $\text{Cr}_2\text{O}_3$ -doped) octahedral. The octahedral was compressed at the center of 8 tungsten carbide cubes, each with an 11 mm corner truncation. Further experimental details can be found in ref. [12].

After HPHT equilibration, the recovered carbon sample was examined by high-resolution scanning electron microscopy (HRSEM) by use of a Philips XL30S instrument, transmission electron microscopy (TEM) and electron diffraction by use of a JEOL 3000F instrument. A JEOL ARM 200F aberration corrected TEM operating in the STEM mode was used to acquire the Electron Energy Loss Spectra (EELS).

### 3.Results and discussion

After performing the HPHT experiment it was possible to easily cut the golden capsule by a steel blade, so that the carbon sample was relatively soft providing evidence that it consists of mainly  $sp^2$ -hybridized carbon. Fig. 1a shows the appearance of the capsule with the carbon sample in the middle indicating that the carbon sample has a dark-grey color. Fig.1b shows its HRSEM image indicating the presence of fine precipitates (below roughly 100 nm) embedded in an apparently amorphous matrix.

Fig. 2a to Fig.2c show TEM images of the carbon sample taken at different magnifications. It can be seen that there are a number of apparently crystalline lamellar nano-grains in the sample of nearly 30 to 50 nm in size. It would appear that the nano-grains are embedded in a poorly crystalline or amorphous carbon matrix.

A number of diffraction patterns, a typical example of which is shown in Fig. 3d, were taken from different areas of the sample. Most areas display the typical pattern of diamond or hexagonal carbon structures. The diffraction pattern shown in Fig. 3d provides clear evidence for the presence of nano-diamond in the sample, as all the reflections of cubic diamond indicated in Fig. 3d can be seen in the electron diffraction pattern.

Fig. 3a and Fig.3b show STEM images of two areas of the carbon sample, where EEL spectra were taken. Fig.4c and Fig.4d show the EEL spectra indicating the presence of mainly amorphous carbon in the sample.

Using equation of state data [13] and under the assumption of ideal mixing it is possible to calculate that under the conditions of the experiment where the oxygen fugacity was buffered by the presence of Mo-MoO<sub>2</sub>, the composition of the fluid formed by the breakdown of adipic acid comprised 60% H<sub>2</sub>O and 40% CH<sub>4</sub>.

Thus, the carbon sample obtained from adipic acid at ultra-high pressures consists of diamond nano-grains embedded in the amorphous or poorly crystallized carbon matrix. The carbon sample comprises mainly  $sp^2$ -hybridized carbon in form of graphite or amorphous carbon. No additional metastable forms of carbon, which were expected to form as a result of the presence of high-pressure water vapor in the capsule during the HPHT experiment, were found in the sample. Nevertheless, the formation of nano-diamond at the relatively low temperature used in this work (1235°C) provides evidence that the employment of adipic acid as a precursor can

simplify the nano-diamond synthesis, as conventionally nano-diamond is obtained at significantly higher temperatures (usually above 1600°C) [11].

#### **4. Conclusions**

Adipic acid was used in this work as a precursor for the HPHT synthesis of the carbon sample containing grains of nano-diamond. The carbon sample consists of lamellar diamond nano-grains of nearly 30 to 50 nm embedded in the amorphous carbon matrix. The majority of the carbon sample comprises  $sp^2$ -hybridized carbon in form of graphite or amorphous carbon.

#### **Acknowledgement**

One of the co-authors (I.Konyashin) gratefully acknowledges the financial support from the Ministry of Education and Science of the Russian Federation in the framework of the Increase Competitiveness Program of MISiS.


#### **References**

- [1] F.P. Bundy, Direct Conversion of Graphite to Diamond in Static Pressure Apparatus, *Science*, 137 (1962) 1057–1058.
- [2] S. Naka, K. Horii, Y. Takeda, T. Hanawa, Direct conversion of graphite to diamond under static pressure, *Nature*. 259 (1976) 38–39.
- [3] H. Yusa, Nanocrystalline diamond directly transformed from carbon nanotubes under high pressure, *Diamond Relat Mater*, 11 (2002) 87–91.
- [4] T. Irifune, A. Kurio, S. Sakamoto, T. Inoue, H. Sumiya, Materials: Ultrahard polycrystalline diamond from graphite, *Nature*. 421 (2003) 599–600.
- [5] H. Sumiya, T. Irifune, Indentation hardness of nano-polycrystalline diamond prepared from graphite by direct conversion, *Diam. Relat. Mater.* 13 (2004) 1771–1776.
- [6] H. Sumiya, T. Irifune, Hardness and deformation microstructures of nano-polycrystalline diamonds synthesized from various carbons under high pressure and high temperature, *J Mater Res*, 22 (2007) 2345–2351.
- [7] H. Sumiya, K. Harano, Distinctive mechanical properties of nano-polycrystalline diamond synthesized by direct conversion sintering under HPHT, *Diamond Relat Mater*, 24 (2012) 44–48.

- [8] K. Harano, T. Satoh, H. Sumiya, Cutting performance of nano-polycrystalline diamond, *Diam Relat Mater*, 24 (2012) 78–82.
- [9] H. Ohfuji, S. Okimoto, T. Kunimoto, F. Isobe, H. Sumiya, K. Komatsu, et al., Influence of graphite crystallinity on the microtexture of nano-polycrystalline diamond obtained by direct conversion, *Phys Chem Miner*, 39 (2012) 543–552.
- [10] F. Isobe, H. Ohfuji, H. Sumiya, T. Irifune, Nanolayered diamond sintered compact obtained by direct conversion from highly oriented graphite under high pressure and high temperature, *J. Nanomater.* 2013 (2013).
- [11] H. Sumiya, H. Yusa, T. Inoue, H. Ofuji, T. Irifune, Conditions and mechanism of formation of nano-polycrystalline diamonds on direct transformation from graphite and non-graphitic carbon at high pressure and temperature, *High Press. Res.* 26 (2006) 63–69.
- [12] Frost D J, Poe B T, Tronnes R G, Liebske C, Duba A, Rubie DC, A New Large-Volume Multianvil System. *Phys. Earth Planet. Int.*, 143-44 (2004) 507-514.
- [13] Belonoshko A B, Saxena S K, A unified equation of state for fluids of CHONS-Ar composition and their mixtures up to very high temperatures and pressures. *Geochim. Cosmochim. Acta* 56 (1992) 3611-3626.




a

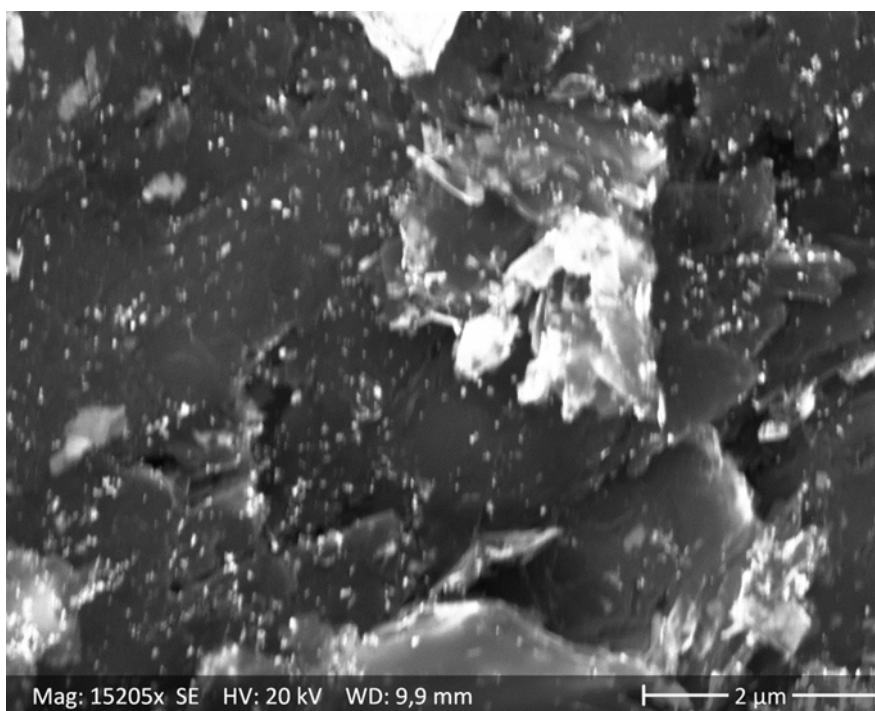


b


Figure 1. Appearance of the carbon sample after the HPHT process: a – golded capsule with the carbon sample, and b – HRSEM image of the carbon sample.

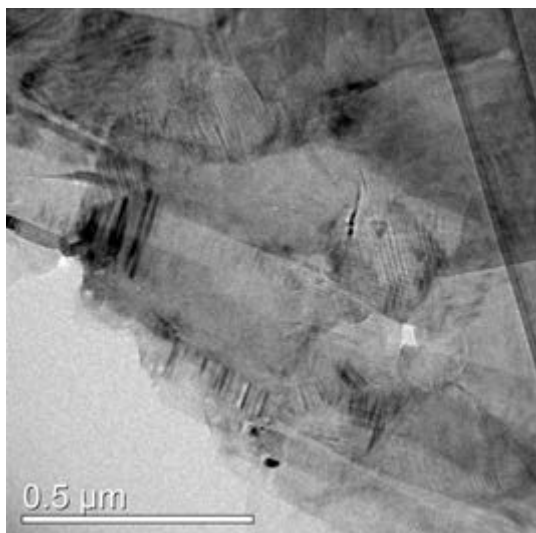


a

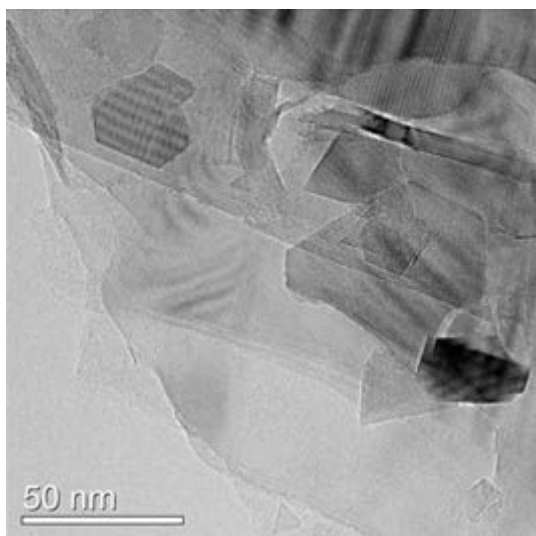

b

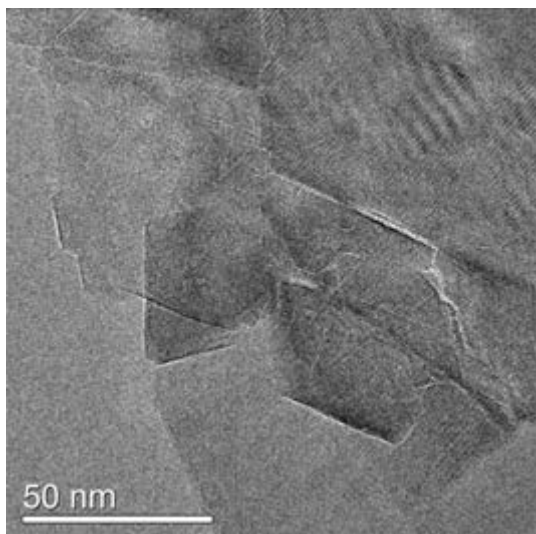


c

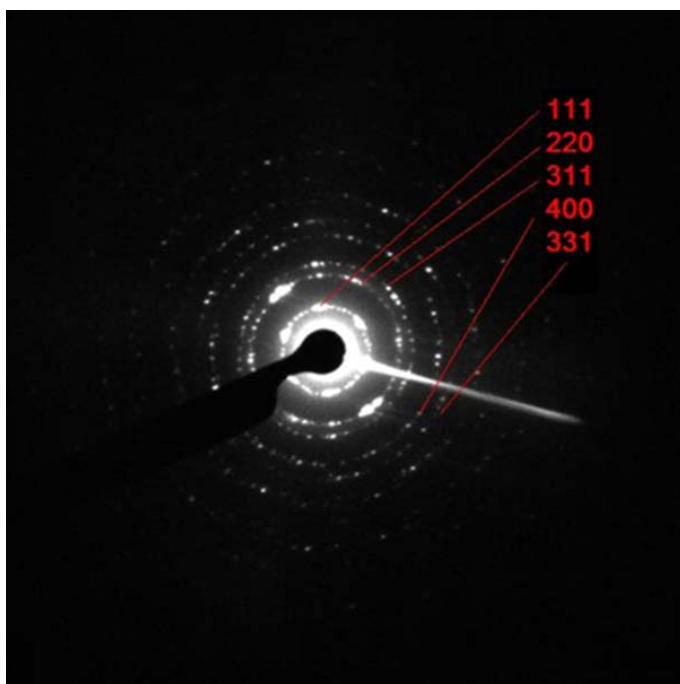


d

Figure 2. TEM images of the carbon sample: a – overview at a low magnification, b and c – different regions of the sample taken at a high magnification; and d - typical electron diffraction pattern from the sample indicating the presence of nano-diamond grains.

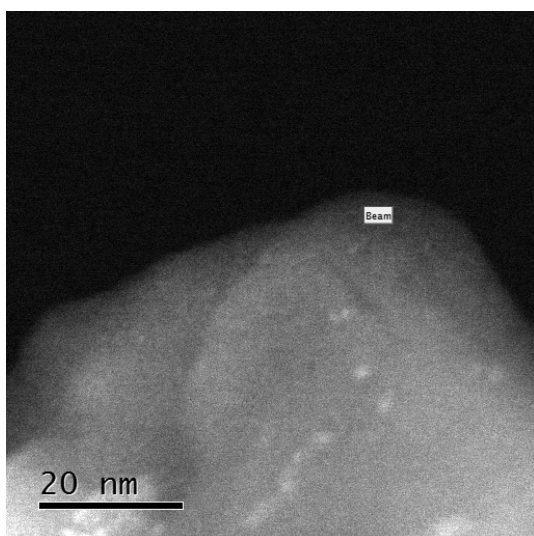


a

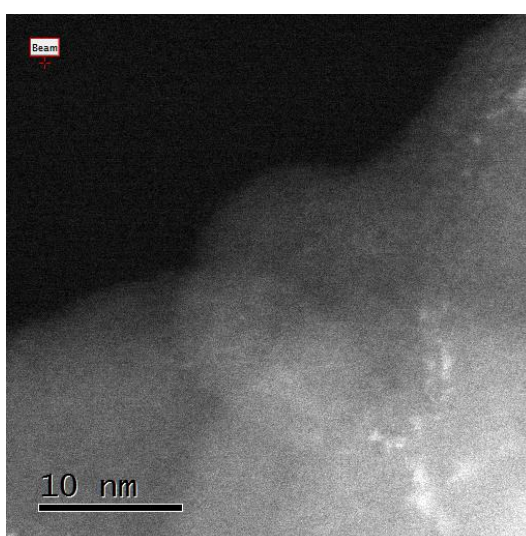


b



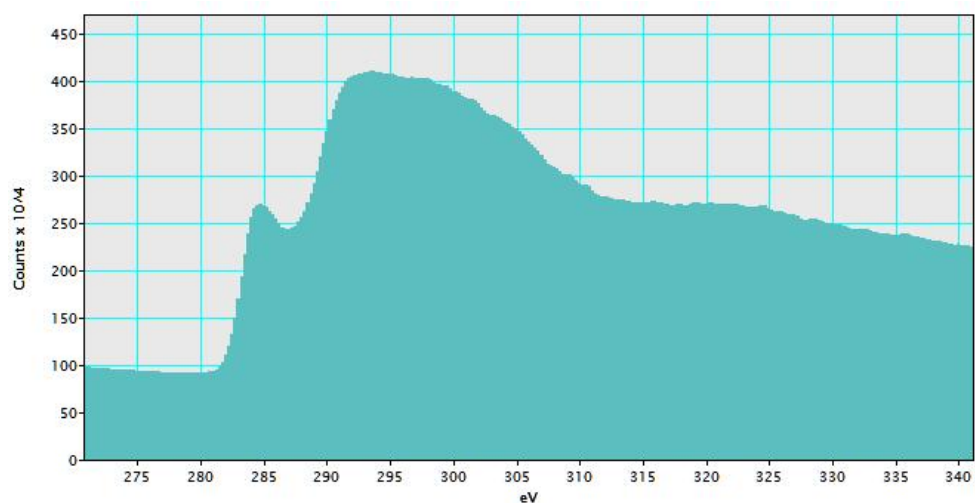

c

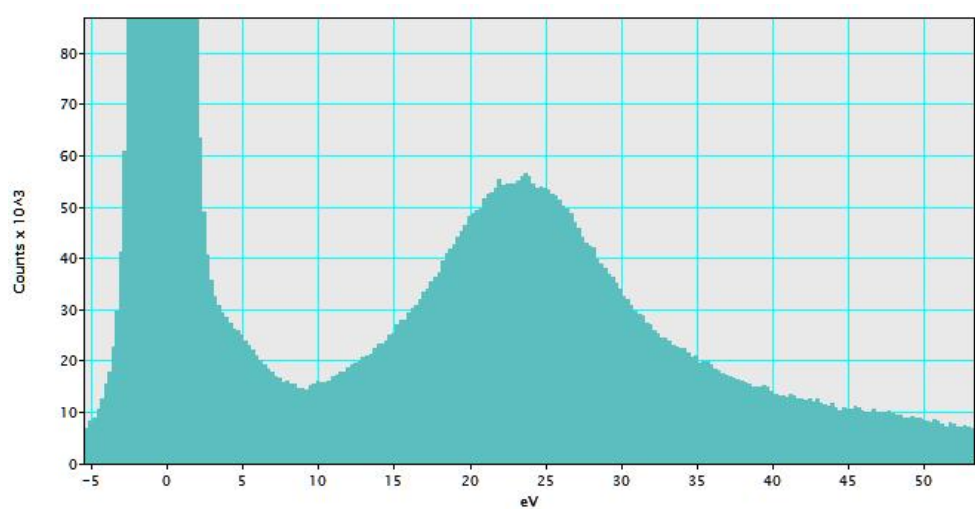

d

Figure 3. STEM images (a and b) and EEL spectra (c and d) from large areas of the carbon sample indicating that the carbon matrix consists of amorphous  $sp^2$ -hybridized carbon.