

Neutral Colour Semi-Transparent Micro-Structured Perovskite Solar Cells

*Giles E. Eperon, Victor M. Burlakov, Alain Goriely and Henry J. Snaith**

[*] Dr. H. J. Snaith, Giles E. Eperon


Department of Physics, University of Oxford, Clarendon Laboratory, Parks Road, Oxford OX1 3PU, UK

E-mail: h.snaith1@physics.ox.ac.uk

Dr. Victor M. Burlakov, Prof. Alain Goriely

Mathematical Institute, OCCAM, University of Oxford, 24-29 St Giles', Oxford OX1 3LB, UK

Table of Contents Graphic

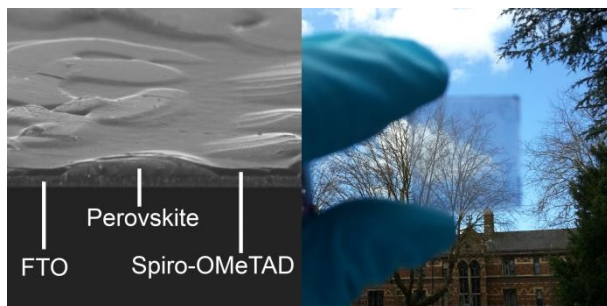

Keywords: perovskite, solar cell, semi-transparent, photovoltaics, building-integrated photovoltaics, neutral colour, micro-structured

Abstract

Neutral-coloured semi-transparent solar cells are commercially desired to integrate solar cells into the windows and cladding of buildings and automotive applications. Here, we report the use of morphological control of perovskite thin-films to form semi-transparent planar heterojunction solar cells with neutral colour and comparatively high efficiencies. We take advantage of spontaneous dewetting to create micro-structured arrays of perovskite “islands”, on a length-scale small enough to appear continuous to the eye yet large enough to enable un-attenuated transmission of light between the islands. The islands are thick enough to absorb most visible light and the combination of completely absorbing and completely transparent regions results in neutral transmission of light. Using these films, we fabricate thin-film solar cells with respectable power conversion efficiencies. Remarkably, we find that such discontinuous films still have good rectification behaviour and relatively high open-circuit voltages due to the inherent rectification between the n- and p-type charge collection layers. Furthermore, we demonstrate the ease of “colour-tinting” such micro-structured perovskite solar cells with no reduction in performance, by incorporation of a dye within the hole transport medium.

Building-integrated photovoltaics (BIPV) are an attractive concept for economic generation of solar power.¹ Integration of semi-transparent solar cells into windows is of particular interest since it opens the prospect of employing the entire façade of a building for solar power generation, rather than simply employing the limited roof space. In order for such solar glazing to be practical, costs must be low, and ideally they can be manufactured through existing coating methods employed in the glazing industry. They need to generate significant power, whilst still having good transparency. Furthermore, whilst coloured windows are interesting for novel applications, and a “splash” of colour is desirable, the largest demand is for neutral-colour tinted windows with controllable levels of transparency.

Some of the most successful approaches to achieve semi-transparency in solar cells have used organic or dye-sensitized solar cells (OPV and DSSC respectively).²⁻⁷ These technologies are solution-processable, representing a low-cost production method and easy scalability.⁸ Impressive recent progress has been made with neutral coloured OPV.^{7,9,10} However, their efficiencies are unlikely to reach those of crystalline technologies in the near future, due to large energy losses occurring at charge transfer interfaces.^{11,12} To attain colour-neutrality with organics, the active materials must be chosen carefully, often at a loss to overall efficiency.^{3,4,13} An option with thin-film solar technologies, where the solar cell comprises a solid absorber layer, is to simply reduce the thickness of the absorber layer to allow transparency. Indeed, this is precisely what is done with amorphous silicon, currently being installed in BIPV applications. However, due to the precise nature of the density of states in the conduction and valence band in a crystalline semiconductor, the absorption coefficient increases monotonically from the band gap, and thin films will assume a red or brown tint. Even though “bronze” is a choice for solar glazing, it does not represent the most desirable option.

Semiconducting perovskites have recently emerged as a new and intriguing class of photovoltaic materials. They have properties similar to bulk inorganic semiconductors, but can be processed at low temperatures using inexpensive and abundant materials.¹⁴⁻²⁰ They have now demonstrated surprisingly high power conversion efficiencies of over 15% in a range of device configurations.^{21,22} Our recent work has shown that high-efficiency

$\text{CH}_3\text{NH}_3\text{PbI}_{3-x}\text{Cl}_x$ perovskite solar cells can be produced at low temperatures and in a fully planar thin-film architecture, reducing fabrication steps and simplifying the design.^{18,23} These characteristics make such perovskites ideal materials for fabrication of semi-transparent windows. However, they fall firmly within the thin-film category and a thin continuous perovskite film suffers from the same reddish-brown tint as conventional semiconductors.

We have recently investigated and developed a methodology to control the fractional surface coverage of $\text{CH}_3\text{NH}_3\text{PbI}_{3-x}\text{Cl}_x$ perovskite films, with the target of obtaining uniform and complete coating.²³ Perovskite films are deposited from spin-coating a precursor with a molar excess of organic and halide components and typically contain several small pores as-cast. Upon annealing, mass loss of the solvent and excess organic (CH_3NH_3) and halide (I or Cl) components allows morphological change due to minimisation of surface energy.²³ The evolution of morphology depends upon several parameters. We found that by controlling parameters such as the initial film thickness, annealing temperature, atmosphere, and solvent vapour pressure, we could control whether pores in general opened or closed, and as such achieved close to 100% surface coverage and highly efficient planar heterojunction solar cells.^{23,24}

In addition to maximising surface coverage, we can make use of incomplete surface coverage. Herein, we leverage dewetting of such films to form micro-structured arrays of perovskite “islands”. The perovskite islands are thick enough to absorb all visible light, whereas the “dewet” regions (absent of perovskite) are visibly transparent. As such, we form a semi-transparent layer whilst avoiding the brown tint observed in thin semiconductor films; the overall optical appearance of such a film is neutral-coloured. By varying the extent of dewetting, we control the transparency of the film, resulting in tuneable and efficient semi-transparent solar cells. This work now endows the perovskite technology with the neutral uniform colouration previously exclusive to organics.

Results and Discussion

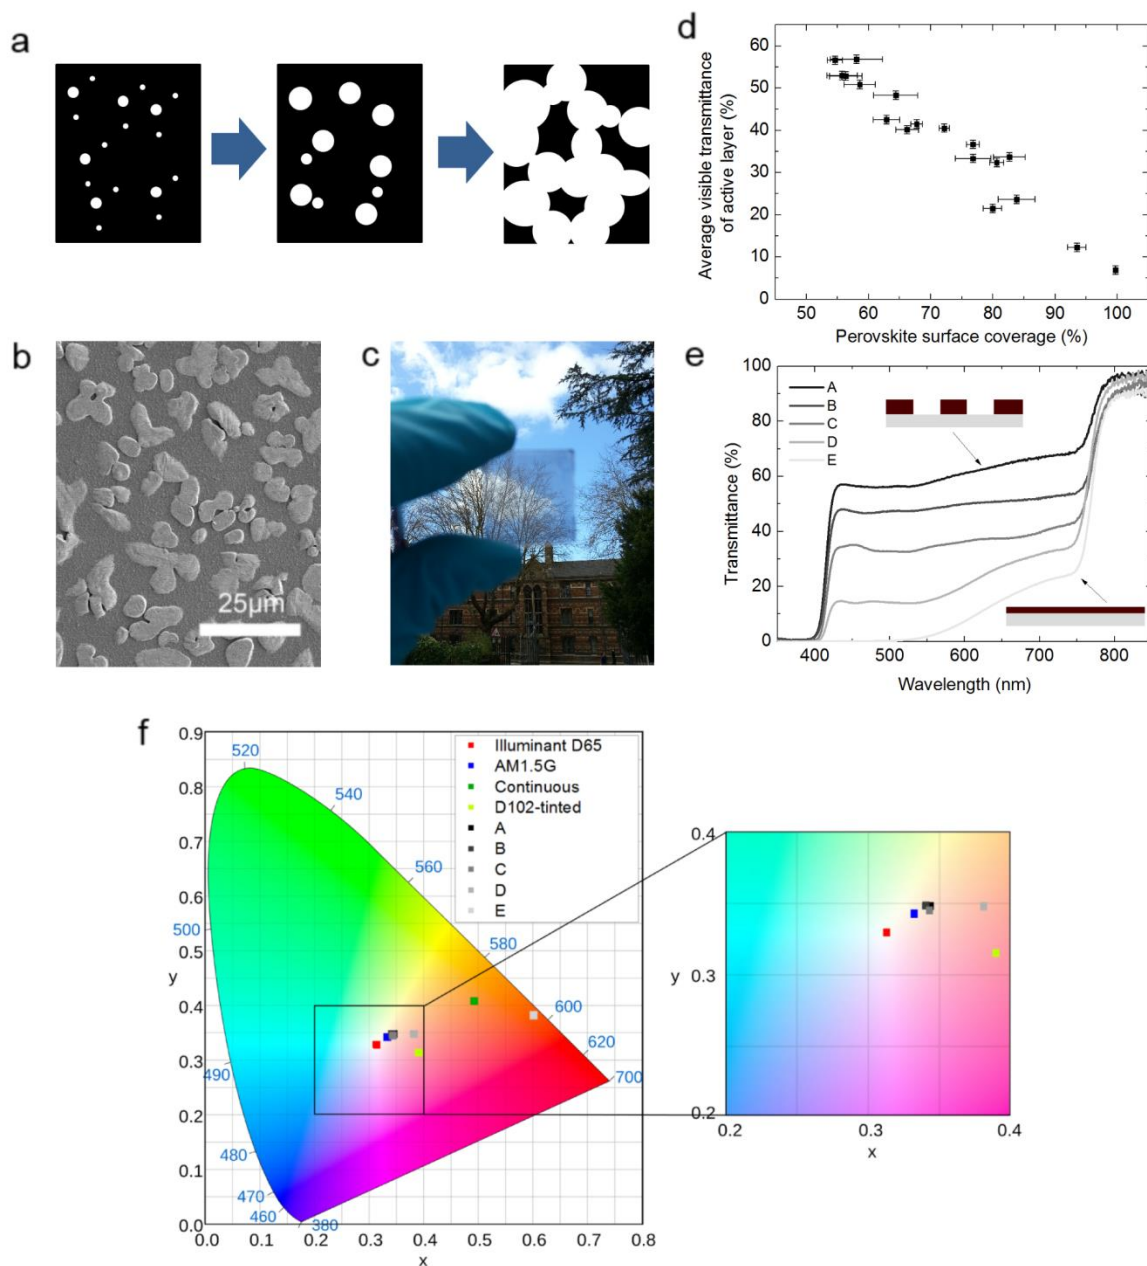


Figure 1: Controlled dewetting to vary transmittance of a perovskite film. **a**, Schematic of the film dewetting process showing morphology change over time, from as-cast film to discrete "islands". Perovskite material is represented with black, pores by white. **b**, Scanning electron micrograph of the top surface of a representative film of perovskite "islands" (paler regions) on a TiO_2 -coated FTO substrate. **c**, Photograph through a typical semi-transparent perovskite film formed on glass, demonstrating neutral colour and semi-transparency. **d**, Dependence of average visible transmittance of the active layer on perovskite surface coverage **e**, Transmittance spectra of

active layers of a selection of dewet perovskite devices. Diagrammatical representations of the most and least transparent films are shown as insets. f, colour coordinates of the films with transmittance spectra shown in (d) under AM1.5 illumination, on the CIE xy 1931 chromacity diagram, and the enlarged central region. Colour coordinates of a thin continuous perovskite film, a D102 dye-tinted cell (described later), the D65 standard daylight illuminant and AM1.5 illumination are also shown.

In Fig. 1a, we show a schematic of the dewetting process to produce discontinuous regions of the perovskite absorber $\text{CH}_3\text{NH}_3\text{PbI}_{3-x}\text{Cl}_x$. Over time, pore growth, controllable through processing conditions such as temperature and film thickness, dictates the final morphology of the polycrystalline film. In Fig. 1b, we show an SEM image of a representative semi-transparent perovskite film formed to maximise open area. We measured the “islands” to be $>1\mu\text{m}$ in height. Visibly, such films appear neutral-coloured (Fig. 1c)- a $1\mu\text{m}$ film of perovskite absorbs effectively all light at energies above its bandgap, which is 1.55eV .²⁰ A continuous $1\mu\text{m}$ film would hence appear black, but because the perovskite film is formed of discontinuous islands, it appears semi-transparent and of neutral colour. For neutral colour to be achieved, it is a prerequisite that the absorption onset of the absorber is in the near infra-red. In order to characterise such films for their use in working solar cells, we are interested in the optical behaviour of not just the perovskite, but the whole active layer necessary to produce a working solar cell. Here, the device architecture is a planar heterojunction of perovskite between an n-type compact TiO_2 layer and a p-type hole transporter, 2,2',7,7'-tetrakis-(N,N-di-p-methoxyphenylamine)9,9'-spirobifluorene (spiro-OMeTAD). As such, from now we define the “active layer” as the structure: compact TiO_2 /perovskite/spiro-OMeTAD. Furthermore, as the application for semi-transparent solar cells is for visible aesthetics, we are interested in the visible wavelengths, between 370 and 740nm. We define the average visible transmittance (AVT) as the mean transmittance of a film between these wavelengths. We fabricated perovskite films on compact TiO_2 -coated FTO glass under a range of processing conditions (see SI) in order to achieve a wide range of transparencies. We measured the perovskite surface coverage *via* analysis of SEM images, then applied the spiro-OMeTAD layer and measured the AVT with an integrating sphere (details in SI). In Figure 1d we show the dependence of AVT on perovskite surface coverage. A linear trend demonstrates the ease of controlling the transparency of such films by carefully choice of solvent and processing temperature. We show a selection of

representative active layer transmittance spectra in Fig. 1e. We see encouragingly flat spectra across the majority of the visible spectrum, especially for the more transmissive samples. For the less transmissive samples (especially D and E in Fig. 1e), there is a higher perovskite surface coverage, or less dewetting. These films were fabricated from the same solution concentrations and spin-coating protocol, but simply using different solvents, and dried and crystallized at different temperatures between 90 to 130 °C. For the same amount of starting material, the final film volume should be the same regardless of the extent of dewetting, hence the regions of perovskite in the films with more coverage are thinner, and evidentially not thick enough to fully absorb the light at the red end of the spectrum. This is seen in Fig 1e, where even with 100% perovskite coverage, AVT is not 0%. The more dewet films comprise thicker perovskite islands and hence have flatter spectra. Diagrams of the cross-section of high and low transmission films are shown as an inset to Fig. 1e.

To quantify the colour-neutrality of the active layers, we calculated colour perception indices using the CIE 1931 xy colour space, designed to represent human visual colour perception. The transmitted light is represented by the product of the AM1.5 solar spectrum and the transmission spectrum of the active layer in question.^{3,25} We calculated x and y colour parameters for the samples labelled A-E in Fig. 1e and display the results on the CIE 1931 xy chromacity diagram in Fig. 1f. We also plot a ~200nm thick continuous perovskite film, the reference daylight illuminant D65 and the AM1.5 spectrum. The colour co-ordinates of the most transmissive active layers (A,B,C) are located very close to the AM1.5 spectrum and the D65 reference in the low colourfulness region of the chromacity diagram, representing excellent colour-neutrality. At lower transmittances, films move towards the red-brown side of the chromacity diagram, where the thin continuous perovskite film is positioned.

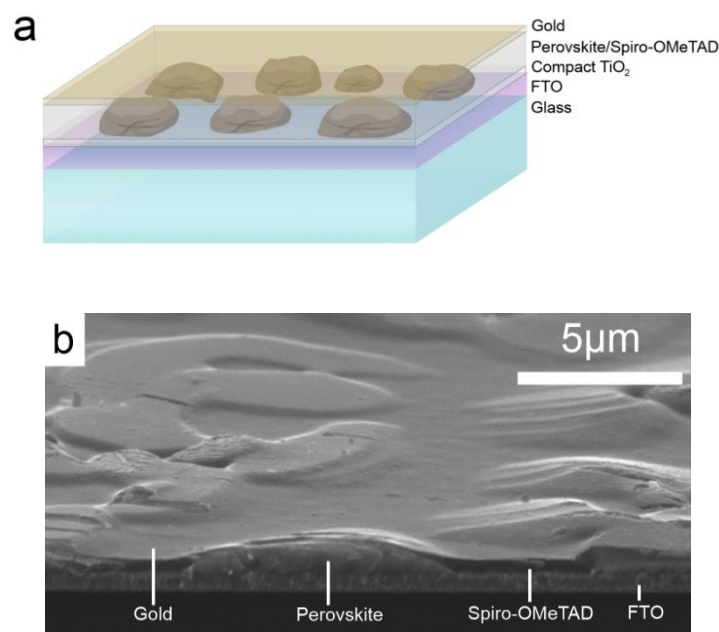


Figure 2: Semi-transparent neutral-coloured perovskite solar cells. ***a**, Diagram showing the architecture of the dewet planar perovskite heterojunction solar cell. **b**, Tilted cross-sectional SEM image of a full semi-transparent solar cell showing the perovskite "islands" coated with spiro-OMeTAD.*

We fabricated planar heterojunction solar cells with a range of transmittances, with the architecture shown in Fig. 2a. An SEM image of a cross section of a full device is shown in Fig. 2b. The perovskite islands can be clearly seen, with the spiro-OMeTAD infiltrating the spaces between and also coating the islands with a thin layer. Ideally we would use extremely transparent and conductive electrodes on both sides in order to maintain high transparencies. However, full optimisation of the electrodes is beyond the scope of this study, and here we used fluorene doped tin oxide (FTO) as the anode and a thin ($\sim 10\text{nm}$) layer of gold as the cathode. Such devices are reasonably transparent, though the gold electrode is a major source of transmittance loss (see SI Fig. S3).

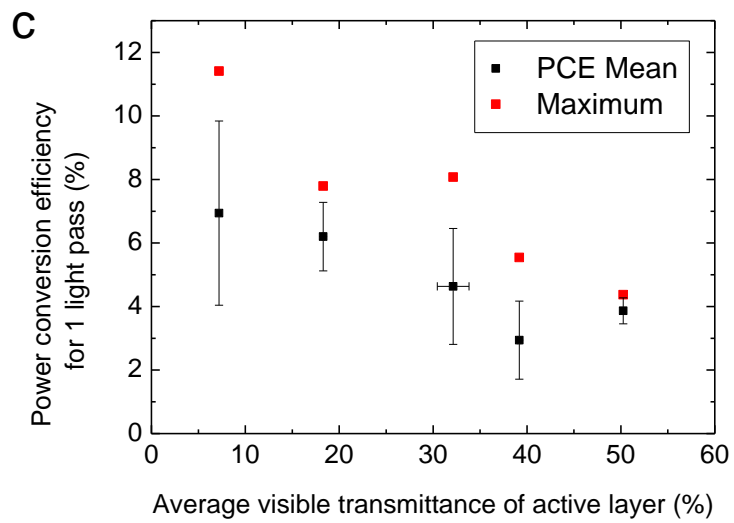
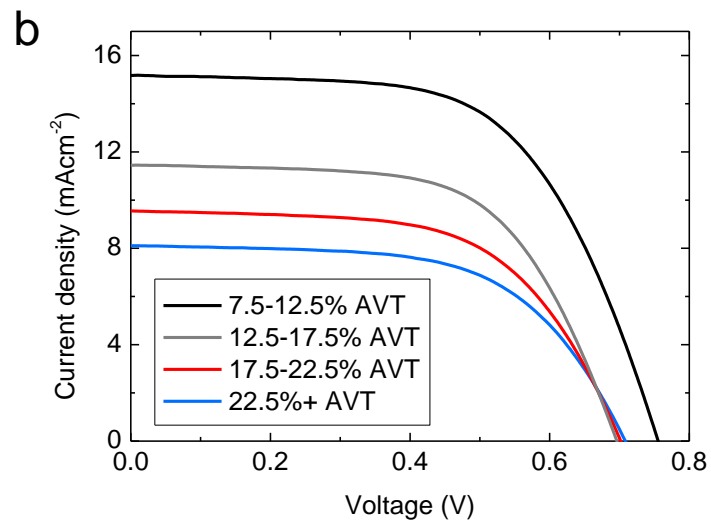
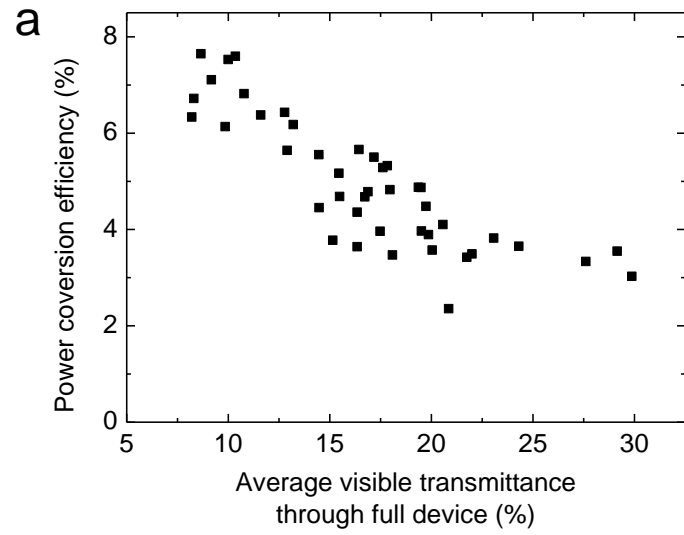




Figure 3: Semi-transparent solar cell device performance. **a**, Power conversion efficiencies for a batch of individual solar cells with $\sim 10\text{nm}$ Au electrodes, plotted as a function of full device AVT. **b**, Average current density-voltage (JV) characteristics for the cells plotted in (a). The curves are numerical averages of the current-voltage characteristics for individual cells split into the AVT intervals shown, with 5-15 cells per interval. **c**, Power conversion efficiency plotted as a function of active layer AVT, for a different batch of cells with thicker gold electrodes. The PCE plotted represents that which is attainable with an entirely transparent cathode (not a thick gold cathode). It has been corrected to remove current generated in the second pass (see SI for details on calculation). Each point represents the mean of at least 14 individual devices, and the maximum PCE for the champion device in each interval is plotted. In all cases PCE was extracted from current-voltage measurements performed under 100mWcm^{-2} AM1.5 illumination. Full performance data for all devices in this Figure are shown in SI tables ST1 and ST2.

In Fig. 3a we plot the power conversion efficiencies against the AVT of the whole device (including 10nm gold electrode) from a single batch of devices, extracted from current density-voltage curves measured under simulated AM1.5, 100mWcm^{-2} sunlight. We observe a clear trend, at the lowest transmittances in this batch (AVT $\sim 7\%$) power conversion efficiencies approach 8%, and as transmittance increases, the efficiency decreases. The most transparent cells, with AVTs of $\sim 30\%$, showed power conversion efficiencies of around 3.5%. In Fig. 3b we show average current density-voltage curves from the same devices split into intervals of AVT. We observe a reduction in photocurrent for the higher transmittance devices, as expected more light passes straight through the device. Remarkably, we find that device yield in these highly discontinuous films does not suffer from critical shunting, as might be expected based on other thin film solar cells. Although there is a significant spread in device efficiency at similar transmittances, few devices were entirely non-functioning, and the lower coverage films did not show a greater spread. An interesting observation is that open-circuit voltage (V_{oc}) is similar at $\sim 0.7\text{V}$ for all but the least transmissive set of cells, where it is raised to $\sim 0.75\text{V}$. We propose that greater perovskite coverage reduces spiro-OMeTAD-compact TiO_2 contact area and these regions represent a parallel diode to the photoactive regions, with a lower shunt resistance. Hence, increasing the perovskite coverage increases the overall shunt resistance and increases the V_{oc} . From these J-V curves it appears that for the higher transmittances (*i.e.* lower

perovskite coverage), the V_{oc} reaches a minimum of $\sim 0.7V$. To further understand this, we fabricated and tested spiro-OMeTAD-compact TiO_2 diodes. Their diode characteristics show a dark current turn-on at also $\sim 0.7V$ (see SI), so even in the case of there being minimum perovskite coverage, we would not expect the diode turn-on voltage to be any lower than $0.7V$, and hence this sets a lower limit on the open-circuit voltage. With full perovskite coverage, spiro-OMeTAD-perovskite-compact TiO_2 devices have been observed to have an open-circuit voltage of $>1V$.²² Thus, with higher perovskite coverage, the fraction of spiro-OMeTAD-perovskite-compact TiO_2 diode area compared to spiro-OMeTAD-compact TiO_2 will increase, and the effective turn-on voltage of these parallel diodes should increase from $0.7V$ to $>1V$, as seen.

The electrodes used (FTO and 10nm thick gold) are non-optimum transparent electrodes. Much work is being undertaken to develop highly transmissive and conductive electrodes for semi-transparent solar cells and other applications.²⁶ In light of this, we determined the best performance that could be achieved from these solar cells if we could use an entirely transparent cathode. We fabricated devices with a number of different active layer AVTs, between 5% and 50% and deposited slightly thicker gold electrodes to minimise electrode resistance. We determined the power conversion efficiency from measuring current-voltage characteristics, and then corrected the photocurrent to remove the fraction of current generated by the second pass of reflected light from the gold electrode (See SI for details of calculation). We thus determined the PCE that could be attained from devices with entirely transparent cathodes (Fig. 3c). We note that we have not increased the measured photocurrent to account for light absorbed in the FTO and all the “corrected” photocurrents are lower than the measured photocurrents (SI Table ST2). Even so, we can see that significantly improved performance could be achieved in comparison to the devices employing the thin gold electrodes, at a given active layer AVT. Notably, $\sim 30\%$ AVT active layers would still generate power conversion efficiencies of over 8%, which is a transparency and a performance that is compatible with commercial applications, being better than currently offered by a-Si, and would represent the best semi-transparent neutral-coloured solar cell efficiency to date. Once we have resolved the lower open-circuit voltages in these micro-structured perovskite solar cells, the V_{oc} should be able to be pushed up towards $1.1V$ which is achievable in uniform planar heterojunction solar cells,²² which will result in another 20 to 30% increase in relative efficiency. In addition, we are still employing TEC7 FTO coated glass, which

is not the most transmissive conducting layer, further improvements are still possible by simply employing a more transparent anode and an antireflective coating (an estimation of the further increases in efficiency possible are discussed in the SI).

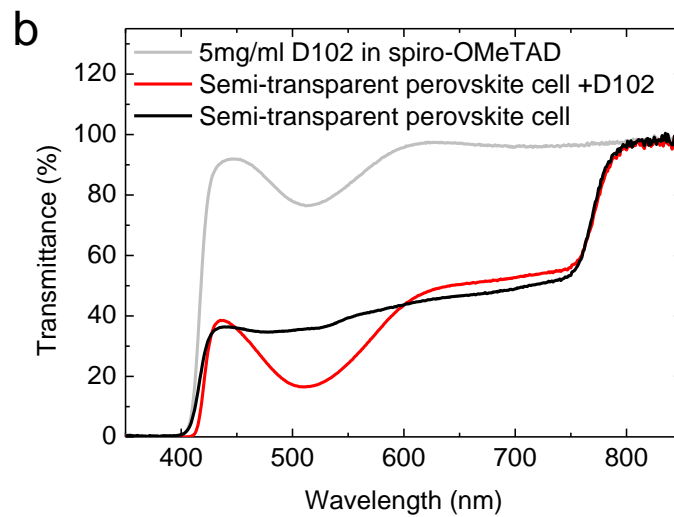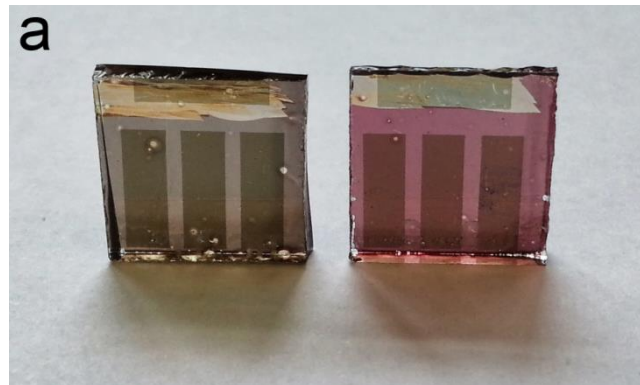

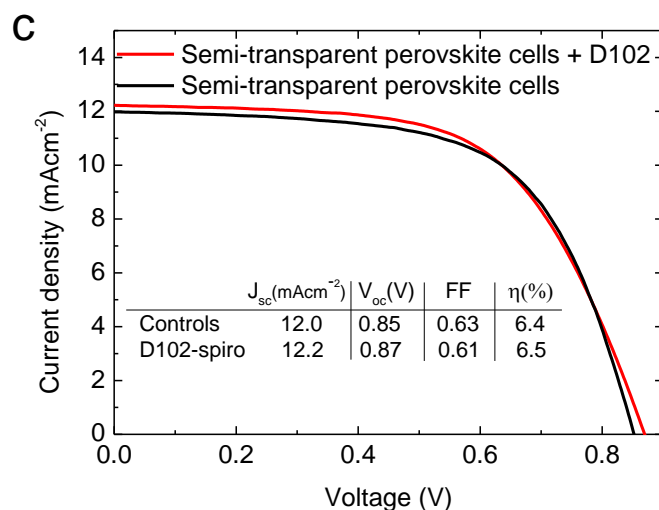


Figure 4: Colour-tinted semi-transparent solar cells. a, Photographs of semi-transparent perovskite solar cells without (left) and with (right) D102 dye included in the spiro-OMeTAD layer, with 10nm gold electrodes. **b,** Transmittance spectra of the active layer of such cells. **c,** Average current density-voltage characteristics of such solar cells, demonstrating effectively no change in performance with inclusion of the dye. Device performance parameters are shown in the inset. Averages are numerical averages from 9 D102 doped and 12 control cells.

Having demonstrated a new and versatile means to form neutral-coloured semi-transparent solar cells, of further interest would be the prospect for lightly colour-tinting such cells. With the micro-structured architecture, we can envisage that it should be easy to optically modify the semi-transparent cells by incorporation of a dye or pigment into the regions where light passes through. Here, we simply dissolved an indolene dye termed D102 into the spiro-OMeTAD solution, and upon application to typical semi-transparent cells it produces “rose-tinted” devices (Fig. 4a).²⁷ Plotting this tinted active layer on the chromacity diagram in Fig. 1f shows these films lie in the pale pink region. As we show in Fig. 4b, the absorption peak of the dye in addition to the perovskite attenuation is apparent in the transmittance spectrum. While light absorbed by the dye will not contribute to photocurrent, device performance should remain unaltered provided the dye has not introduced any detrimental electronic

artefacts. We show the current voltage curves of such devices in Fig. 4c which confirm this, on average the rose-tinted cells perform similarly to the control cells.

Another way of providing semi-transparency would be to use a wider bandgap perovskite, of which there are many known examples.^{19,28,29} However, this system would be restricted to the range of colours attainable with such a semiconductor (yellow, though red, to brown); the advantage of dye-tinting a neutral-coloured 'base' is that any colour of dye or pigment could be incorporated, and those with proven resilience to long term exposure to light, and even colours typically challenging to achieve with semiconductors such as green or blue.

There is no 'ideal' semi-transparent solar cell, since it depends upon the colour desired. For an application requiring colours achievable with a semiconductor, a continuous layer of wider bandgap perovskite might be preferable. However, the novelty of the present work is that we have fabricated neutral-coloured semi-transparent solar cells. For colour-neutrality, a bandgap of $\sim 1.6\text{eV}$ or lower is necessary, so that a thick layer absorbs all visible light and hence looks black. This configuration also allows the addition of *any* colour to the grey 'base', providing much greater flexibility in terms of independence of colour and semi-transparency.

As discussed briefly earlier, more transparent electrodes are necessary, specifically the cathode, for fully optimised semi-transparent perovskite solar cells. For this purpose, low temperature processible, and ideally solution processible electrodes need to be developed, which have towards 90% AVT with the order of $10\ \Omega/\square$ sheet resistivity and exhibit good ohmic contact to the hole-transporter. Solutions may come from transparent conducting oxides, carbon nanotubes, graphene or metallic nanowires, such as silver.^{6,26,30–35}

A key concern for an application such as architectural glass is that of long-term stability. Power-generating glass must have a long functional lifetime to avoid the expense of replacing it regularly. The methylammonium lead halide perovskite is hygroscopic, indicating that substantive sealing from the atmosphere is required, facilitated by sealing between two glass sheets. Recent preliminary work on stability has also shown that even with rudimentary sealing from the atmosphere, such solar cells are already relatively robust to prolonged exposure and operation under full spectrum sun light.^{21,36} Ensuring the materials and solar cell composites are capable of

attaining operational lifetimes of over 25 years should attract significant research attention going forward, and is likely to be a surmountable challenge.

Conclusions

In summary, we have demonstrated the fabrication of neutral-coloured semi-transparent solar cells by creating micro-porous layers of organometal halide perovskite by partial dewetting of solution cast films. Our complete devices show good efficiencies at reasonable levels of transparencies, with significant scope for further improvement by implementing electrodes with higher transparencies and enhancing the open-circuit voltage. Furthermore, we have demonstrated that the micro-structured perovskite film concept can be easily adapted to integrate colour into semi-transparent devices, with no loss in efficiency. This work now enables perovskite solar cells to not only compete for high efficiency opaque applications, but to also offer an ideal solution to building integrated photovoltaics; neutral colour semi-transparency at comparatively high efficiency.

Methods

Materials. Unless otherwise stated, all materials were purchased from Sigma-Aldrich or Alfa Aesar and used as received. Spiro-OMeTAD was purchased from Borun Chemicals. $\text{CH}_3\text{NH}_3\text{I}$ was synthesised in-house according to a reported procedure.²⁰

Semi-transparent perovskite solar cell preparation. Devices were fabricated on fluorine-doped tin oxide (FTO) coated glass (Pilkington, $7\Omega\text{ cm}^{-1}$). Initially FTO was removed from regions under the anode contact by etching the FTO with 2M HCl and zinc powder. Substrates were then cleaned sequentially in hallmanex detergent, acetone, propan-2-ol and oxygen plasma. A ~50nm hole-blocking layer of compact TiO_2 was deposited by spin-coating a mildly acidic solution of titanium isopropoxide in ethanol (350ul in 5ml ethanol with 0.013M HCl) at 2000rpm, and annealed at 500°C for 30 minutes.

The dewet perovskite layers were deposited by spin-coating a non-stoichiometric precursor solution of methylammonium iodide and lead chloride (3:1 molar ratio, final concentrations 0.88M lead chloride and 2.64M methylammonium iodide) in either dimethylsulfoxide (DMSO), n-methyl-2-pyrrolidone (NMP) or N,N-

dimethylformamide (DMF) (not mixtures of). The films were then annealed to dewet and crystallise the perovskite. Details of the conditions used to produce a certain active layer transmittance are reported in the supplementary information. Spin-coating and annealing was carried out in either air or a moisture and oxygen-free glovebox ($\text{H}_2\text{O} < 1\text{ppm}$), at 2000rpm. Annealing was carried out at a range of temperatures between 90°C and 130°C.

The hole-transporting layer was then deposited *via* spin-coating a 0.788M solution in chlorobenzene of 2,2',7,7'-tetrakis-(N,N-di-p-methoxyphenylamine)9,9'-spirobifluorene (spiro-OMeTAD), with additives of 0.0184 lithium bis(trifluoromethanesulfonyl)imide (added in 0.61M acetonitrile solution) and 0.0659M 4-tert-butylpyridine. Spin-coating was carried out in air at 2000rpm.

Gold electrodes were thermally evaporated under vacuum of $\sim 10^{-6}$ Torr, at a rate of $\sim 0.1\text{nm/s}$, to complete the devices. For semi-transparent contacts, $\sim 10\text{nm}$ was deposited.

Device Characterisation. The current density–voltage (J-V) curves were measured (2400 Series SourceMeter, Keithley Instruments) under simulated AM 1.5 sunlight at 100mWcm^{-2} irradiance generated by an Abet Class AAB sun 2000 simulator, with the intensity calibrated with an NREL calibrated KG5 filtered Si reference cell. The mismatch factor was calculated to be less than 1%. The solar cells were masked with a metal aperture to define the active area, typically 0.09cm^2 (measured individually for each mask) and measured in a light-tight sample holder to minimize any edge effects and ensure that the reference cell and test cell are located during measurement in the same spot under the solar simulator.

Optical measurements. Transmittance and reflectance spectra were collected with a Varian Cary 300 UV-Vis spectrophotometer with an internally coupled integrating sphere.

Film characterisation: A Hitachi S-4300 field emission scanning electron microscope and a FEI Inspect S50 tungsten source scanning electron microscope were used to acquire SEM images. To determine coverage of perovskite films from SEM images, ImageJ³⁷ was used to define a greyscale threshold such that the perovskite was

distinct from the substrate, and percentage coverage was then calculated by the program. Sample thicknesses were measured using a Veeco Dektak 150 surface profileometer.

Acknowledgments

This work was supported by EPSRC and Oxford Photovoltaics Ltd. through a Nanotechnology KTN CASE award, the European Research Council (ERC) HYPER PROJECT no. 279881. This publication is based in part upon work supported by Award No. KUK-C1-013-04, made by King Abdullah University of Science and Technology (KAUST). AG is a Wolfson/Royal Society Merit Award Holder and acknowledges support from a Reintegration Grant under EC Framework VII. VB is an Oxford Martin School Fellow and this work was in part supported by the Oxford Martin School. The authors wish to thank Maximillian Hoerantner for assistance in graphical design.

Supporting Information

Detailed description of dewetting control, calculations of active layer transmittance, transmissive losses due to gold electrode, correction to remove second pass of light reflected from electrodes, estimation of extra photocurrent available with a fully transparent anode, and current-voltage characteristics for a diode with no perovskite layer. This material is available free of charge *via* the Internet at <http://pubs.acs.org>.

References

1. Henemann, A. BIPV: Built-in Solar Energy. *Renew. Energy Focus* **2008**, 9, 14–19.
2. Kang, M. G.; Park, N.; Park, Y. J.; Ryu, K. S.; H., C. S. Manufacturing Method for Transparent Electric Windows Using Dye-Sensitized TiO₂ Solar Cells. *Sol. Energy Mater. Sol. Cells* **2003**, 75, 475–479.
3. Chen, K.-S.; Salinas, J.-F.; Yip, H.-L.; Huo, L.; Hou, J.; Jen, A. K.-Y. Semi-Transparent Polymer Solar Cells with 6% PCE, 25% Average Visible Transmittance and a Color Rendering Index Close to 100 for Power Generating Window Applications. *Energy Environ. Sci.* **2012**, 5, 9551–9557.
4. Chiang, Y.-F.; Chen, R.-T.; Burke, A.; Bach, U.; Chen, P.; Guo, T.-F. Non-Color Distortion for Visible Light Transmitted Tandem Solid State Dye-Sensitized Solar Cells. *Renew. Energy* **2013**, 59, 136–140.
5. Chueh, C.-C.; Chien, S.-C.; Yip, H.-L.; Salinas, J. F.; Li, C.-Z.; Chen, K.-S.; Chen, F.-C.; Chen, W.-C.; Jen, A. K.-Y. Toward High-Performance Semi-Transparent Polymer Solar Cells: Optimization of Ultra-Thin Light Absorbing Layer and Transparent Cathode Architecture. *Adv. Energy Mater.* **2013**, 3, 417–423.
6. Chen, C.; Dou, L.; Zhu, R.; Chung, C.; Song, T.; Zheng, Y. B.; Hawks, S.; Li, G.; Weiss, P. S.; Yang, Y. Visibly Transparent Polymer Solar Cells Produced by Solution Processing. *ACS Nano* **2012**, 6, 7185–7190.
7. Bailey-Salzman, R. F.; Rand, B. P.; Forrest, S. R. Semitransparent Organic Photovoltaic Cells. *Appl. Phys. Lett.* **2006**, 88, 233502:1–3.
8. Krebs, F. C.; Tromholt, T.; Jørgensen, M. Upscaling of Polymer Solar Cell Fabrication Using Full Roll-to-Roll Processing. *Nanoscale* **2010**, 2, 873–886.
9. Colmann, A.; Puetz, A.; Bauer, A.; Hanisch, J.; Ahlswede, E.; Lemmer, U. Efficient Semi-Transparent Organic Solar Cells with Good Transparency Color Perception and Rendering Properties. *Adv. Energy Mater.* **2011**, 1, 599–603.
10. Chen, C.-C.; Dou, L.; Gao, J.; Chang, W.-H.; Li, G.; Yang, Y. High-Performance Semi-Transparent Polymer Solar Cells Possessing Tandem Structures. *Energy Environ. Sci.* **2013**, 6, 2714–2720.
11. Snaith, H. J. Estimating the Maximum Attainable Efficiency in Dye-Sensitized Solar Cells. *Adv. Funct. Mater.* **2010**, 20, 13–19.
12. Kirchartz, T.; Taretto, K.; Rau, U. Efficiency Limits of Organic Bulk Heterojunction Solar Cells. *J. Phys. Chem. C* **2009**, 113, 17958–17966.
13. Ameri, T.; Dennler, G.; Waldauf, C.; Azimi, H.; Seemann, A.; Forberich, K.; Hauch, J.; Scharber, M.; Hingerl, K.; Brabec, C. J. Fabrication, Optical Modeling, and Color Characterization of Semitransparent Bulk-Heterojunction Organic Solar Cells in an Inverted Structure. *Adv. Funct. Mater.* **2010**, 20, 1592–1598.

14. Kim, H.-S.; Lee, C.-R.; Im, J.-H.; Lee, K.-B.; Moehl, T.; Marchioro, A.; Moon, S.-J.; Humphry-Baker, R.; Yum, J.-H.; Moser, J. E.; *et al.* Lead Iodide Perovskite Sensitized All-Solid-State Submicron Thin Film Mesoscopic Solar Cell with Efficiency Exceeding 9%. *Sci. Rep.* **2012**, *2*, 591:1–7.
15. Im, J.-H.; Lee, C.-R.; Lee, J.-W.; Park, S.-W.; Park, N.-G. 6.5% Efficient Perovskite Quantum-Dot-Sensitized Solar Cell. *Nanoscale* **2011**, *3*, 4088–4093.
16. Kojima, A.; Teshima, K.; Shirai, Y.; Miyasaka, T. Organometal Halide Perovskites as Visible-Light Sensitizers for Photovoltaic Cells. *J. Am. Chem. Soc.* **2009**, *131*, 6050–6051.
17. Chung, I.; Lee, B.; He, J.; Chang, R. P. H.; Kanatzidis, M. G. All-Solid-State Dye-Sensitized Solar Cells with High Efficiency. *Nature* **2012**, *485*, 486–489.
18. Ball, J. M.; Lee, M. M.; Hey, A.; Snaith, H. J. Low-Temperature Processed Mesosuperstructured to Thin-Film Perovskite Solar Cells. *Energy Environ. Sci.* **2013**, *6*, 1739–1743.
19. Noh, J. H.; Im, S. H.; Heo, J. H.; Mandal, T. N.; Seok, S. II Chemical Management for Colorful, Efficient, and Stable Inorganic-Organic Hybrid Nanostructured Solar Cells. *Nano Lett.* **2013**, *13*, 1764–1769.
20. Lee, M. M.; Teuscher, J.; Miyasaka, T.; Murakami, T. N.; Snaith, H. J. Efficient Hybrid Solar Cells Based on Meso-Superstructured Organometal Halide Perovskites. *Science* **2012**, *338*, 643–647.
21. Burschka, J.; Pellet, N.; Moon, S.-J.; Humphry-Baker, R.; Gao, P.; Nazeeruddin, M. K.; Grätzel, M. Sequential Deposition as a Route to High-Performance Perovskite-Sensitized Solar Cells. *Nature* **2013**, *499*, 316–319.
22. Liu, M.; Johnston, M. B.; Snaith, H. J. Efficient Planar Heterojunction Perovskite Solar Cells by Vapour Deposition. *Nature* **2013**. doi:10.1038/nature12509
23. Eperon, G. E.; Burlakov, V. M.; Docampo, P.; Goriely, A.; Snaith, H. J. Morphological Control for High Performance, Solution-Processed Planar Heterojunction Perovskite Solar Cells. *Adv. Funct. Mater.* **2013**. doi:10.1002/adfm.201302090
24. Stranks, S. D.; Eperon, G. E.; Grancini, G.; Menelaou, C.; Alcocer, M. J. P.; Leijtens, T.; Herz, L. M.; Petrozza, A.; Snaith, H. J. Electron-Hole Diffusion Lengths Exceeding 1 Micron in an Organometal Trihalide Perovskite Absorber. *Science* **2013**, *342*, 341–344.
25. Smith, T.; Guild, J. The CIE Colorimetric Standards and Their Use. *Trans. Opt. Soc.* **1932**, *33*, 73–134.
26. Ellmer, K. Past Achievements and Future Challenges in the Development of Optically Transparent Electrodes. *Nat. Photonics* **2012**, *6*, 809–817.
27. Schmidt-Mende, L.; Bach, U.; Humphry-Baker, R.; Horiuchi, T.; Miura, H.; Ito, S.; Uchida, S.; Grätzel, M. Organic Dye for Highly Efficient Solid-State Dye-Sensitized Solar Cells. *Adv. Mater.* **2005**, *17*, 813–815.

28. Im, J.-H.; Chung, J.; Kim, S.-J.; Park, N.-G. Synthesis , Structure , and Photovoltaic Property of a Nanocrystalline 2H Perovskite-Type Novel Sensitizer CH₃CH₂NH₃PbI₃. *Nanoscale Res. Lett.* **2012**, *7*, 353.
29. Mitzi, D. B. *Progress in Inorganic Chemistry, Volume 48*; Karlin, K. D., Ed.; John Wiley & Sons, Inc, 1999; pp. 1–122.
30. Gaynor, W.; Burkhard, G. F.; McGehee, M. D.; Peumans, P. Smooth Nanowire/polymer Composite Transparent Electrodes. *Adv. Mater.* **2011**, *23*, 2905–10.
31. Krantz, J.; Stubhan, T.; Richter, M.; Spallek, S.; Litzov, I.; Matt, G. J.; Spiecker, E.; Brabec, C. J. Spray-Coated Silver Nanowires as Top Electrode Layer in Semitransparent P3HT:PCBM-Based Organic Solar Cell Devices. *Adv. Funct. Mater.* **2012**, *23*, 1711–1717.
32. Yang, D.; Meng, G.; Zhang, S.; Hao, Y.; An, X.; Wei, Q.; Ye, M.; Zhang, L. Electrochemical Synthesis of Metal and Semimetal Nanotube-Nanowire Heterojunctions and Their Electronic Transport Properties. *Chem. Commun.* **2007**, *1*, 1733–1735.
33. Wu, J.; Becerril, H. a.; Bao, Z.; Liu, Z.; Chen, Y.; Peumans, P. Organic Solar Cells with Solution-Processed Graphene Transparent Electrodes. *Appl. Phys. Lett.* **2008**, *92*, 263302:1–3.
34. Wang, X.; Zhi, L.; Müllen, K. Transparent, Conductive Graphene Electrodes for Dye-Sensitized Solar Cells. *Nano Lett.* **2008**, *8*, 323–327.
35. Lagemaat, J. van de; Barnes, T. M.; Rumbles, G.; Shaheen, S. E.; Coutts, T. J.; Weeks, C.; Levitsky, I.; Peltola, J.; Glatkowski, P. Organic Solar Cells with Carbon Nanotubes Replacing In₂O₃:Sn as the Transparent Electrode. *Appl. Phys. Lett.* **2006**, *88*, 233503:1–3.
36. Leijtens, T.; Eperon, G. E.; Pathak, S.; Abate, A.; Lee, M. M.; Snaith, H. J. Overcoming Ultraviolet Light Instability of Sensitized TiO₂ with Meso-Superstructured Organometal Trihalide Perovskite Solar Cells. *Nat. Commun.* **2013**. doi: 10.1038/ncomms3885
37. Rasband, W. ImageJ **2005**, <http://rsb.info.nih.gov/ij/>.