

# Magnetic ordering in the layered oxyselenides $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ and $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$

---

Sebastian J. C. Herkelrath,<sup>a</sup> Jack N. Blandy,<sup>a,b</sup> and Simon J. Clarke<sup>a,\*</sup>

<sup>a</sup>*Department of Chemistry, University of Oxford, Inorganic Chemistry Laboratory, South Parks Road, Oxford OX1 3QR, United Kingdom.*

<sup>b</sup>*Diamond Light Source Ltd., Harwell Science and Innovation Campus, Didcot OX11 0DE, United Kingdom.*

\* Corresponding author


email address: [simon.clarke@chem.ox.ac.uk](mailto:simon.clarke@chem.ox.ac.uk)

## Abstract

The antiferromagnetic structures of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  are solved using powder neutron diffraction. Both compounds adopt the same magnetic structure, based on a  $\sqrt{2}a \times \sqrt{2}a \times c$  expansion of the nuclear cell with magnetic space group  $P_c4_2/n$  (86.72 in the Belov-Neronova-Smirnova notation). This structure is adopted as a result of nearest-neighbour antiferromagnetic interactions within the  $\text{CoO}_2$  planes. The refined long-range-ordered magnetic moments of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  are  $3.7(1)$  and  $3.97(3) \mu_B$  per Co ion respectively. The refined moments are significantly greater than the value predicted from just considering the spin ( $3 \mu_B$ ); this is attributed to a significant orbital contribution to the magnetic moment in an analogous manner to that previously observed for  $\text{Sr}_2\text{CoO}_2\text{Cu}_2\text{S}_2$  and the values conform to a relationship between the shape of the distended  $\text{CoO}_4\text{Ch}_2$  ( $\text{Ch} = \text{S}, \text{Se}$ ) octahedron and the size of the ordered moment established for a series of related compounds.


Keywords: *Oxychalcogenide; Oxide selenide; antiferromagnetic order*

## Abstract Figure

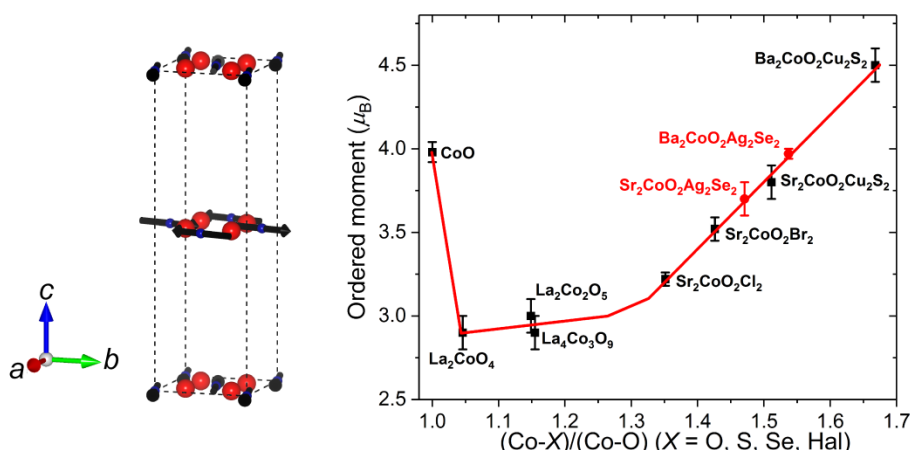

## Introduction

The synthesis and characterisation of the first layered cobalt oxychalcogenides,  $A_2CoO_2Cu_2S_2$  ( $A = Sr, Ba$ ), were reported by Zhu *et al.* [1] These compounds adopted the  $Sr_2Mn_3Sb_2O_{12}$  structure type [2], with alternating square planar  $CoO_2$  and antifluorite-type  $Cu_2S_2$  layers with  $A^{2+}$  cations situated in between, as shown in Figure 1. This structure is adopted by compounds with a wide range of anions and cations as described elsewhere [3].

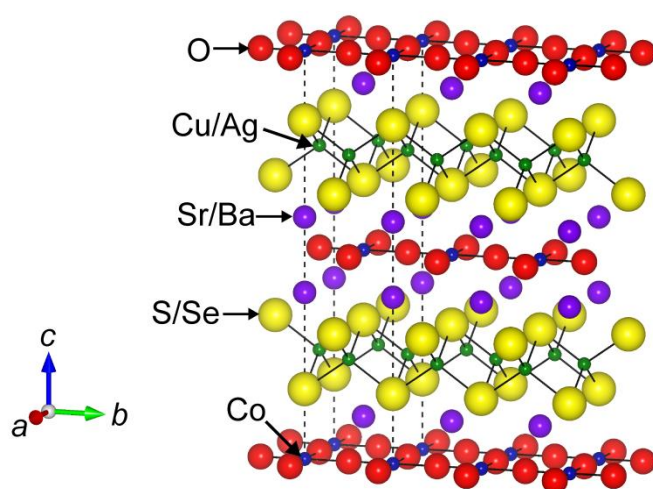

**Figure 1.** The crystal structure of  $A_2CoO_2M_2Ch_2$ , where  $A = Sr, Ba$ ;  $M = Cu, Ag$  and  $Ch = S, Se$ .

These solids have attracted significant interest because they represent an unusual example of high spin  $Co^{2+}$  in a coordination environment that describes a greatly distended  $CoO_4Ch_2$  ( $Ch = S, Se$ ) octahedron which can be considered as tending to square planar (i.e. approaching square planar  $CoO_4$ ). A small copper deficiency in  $Sr_2CoO_2Cu_{2-x}S_2$  was reported by Zhu *et al.* [1], and subsequent work by Smura *et al.* revealed that  $Sr_2CoO_2Cu_2S_2$  could be synthesised stoichiometrically, but a Cu deficiency of up to about 5% was induced by reaction of  $Sr_2CoO_2Cu_2S_2$  with moist air [4]. The same report by Smura *et al.* showed that the magnetic structure of both  $Sr_2CoO_2Cu_2S_2$  and  $Ba_2CoO_2Cu_2S_2$  was based on the antiferromagnetic coupling of nearest-neighbour  $Co^{2+}$  ions within the  $CoO_2$  planes [4]. The refined moment on each  $Co^{2+}$  ion was  $3.81(6) \mu_B$  for stoichiometric  $Sr_2CoO_2Cu_2S_2$  and  $4.45(9) \mu_B$  for  $Ba_2CoO_2Cu_2S_2$ . These values are both much larger than the  $3 \mu_B$  maximum expected for

ordered high spin  $\text{Co}^{2+}$  moments using the spin-only approximation. With the assistance of computation, this discrepancy was attributed to a large unquenched orbital contribution to the magnetic moment which increased as the  $\text{Co}^{2+}$  coordination environment became increasingly square planar [4]. The ordered magnetic moment of a sample of  $\text{Sr}_2\text{CoO}_2\text{Cu}_{2-x}\text{S}_2$  that had been exposed to moist  $\text{O}_2$  was  $2.44(6) \mu_B$ , far below the value obtained for stoichiometric  $\text{Sr}_2\text{CoO}_2\text{Cu}_2\text{S}_2$ . This and several differences in variable temperature magnetometry measurements were attributed to magnetic disorder induced by partial oxidation of the  $\text{Co}^{2+}$  ions in copper-deficient  $\text{Sr}_2\text{CoO}_2\text{Cu}_{2-x}\text{S}_2$  [4].

$\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  are both isostructural with  $\text{Sr}_2\text{CoO}_2\text{Cu}_2\text{S}_2$ , as shown by previous work [5,6]. Both these compounds were shown to be insulators using electrical transport measurements. Magnetic susceptibility measurements revealed broad maxima at 200 – 250 K, characteristic of antiferromagnetic ordering that is primarily two-dimensional in character [5,6]. This work extends the characterisation of these compounds by using powder neutron diffraction to characterise the magnetic ordering behaviour of these compounds at low temperatures, enabling comparison with the analogues containing copper sulfide layers.

## Experimental

**Synthesis.**  $\text{A}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  ( $\text{A} = \text{Sr}, \text{Ba}$ ) samples were made by solid state sintering of a pressed pellet of Se (Alfa Aesar 99.999%), Co (Alfa Aesar Puratronic 99.998%), Ag (99.995% Sigma Aldrich) and BaO (99.99% Sigma Aldrich) or SrO respectively. Pure SrO (according to laboratory PXRD) was prepared from thermal decomposition of  $\text{SrCO}_3$  (Alfa Aesar 99.995%) by heating it for 18 h at 850 °C and for a further 6 h at 1100 °C under dynamic vacuum. The reactants were ground thoroughly in an argon-filled glove box and pressed into one pellet, then loaded into an alumina crucible. Finally, the crucible was sealed in a dried silica tube under vacuum and heated in a furnace for 2 days at 835 °C ( $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ ) or 825 °C ( $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ ).

**Diffraction measurements.** Initial structural characterisation was carried out by powder X-ray diffraction (PXRD) using a PANalytical X'Pert pro instrument operating in Bragg-Brentano geometry with a Ge(111) monochromator to select  $\text{CuK}\alpha_1$  radiation. 3 – 4 g samples of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  were measured using powder neutron diffraction (PND) at room temperature and 5 K in order to determine the magnetic structure of each compound.  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  was measured using the constant-wavelength diffractometer D2B at the Institut Laue Langevin (ILL), Grenoble, France. 1.59 Å neutrons were selected by a Ge(115) crystal monochromator and detected using a multi-angle detector.  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  was measured using the time-of-flight neutron diffractometer POLARIS at ISIS, Didcot, UK using data banks at 35, 90 and 145 degrees  $2\theta$  [7]. Rietveld refinement against both PND and PXRD data were conducted using the TOPAS Academic Version 5 software [8]. The magnetic structure was determined using ISODISTORT [9] in conjunction with TOPAS Academic.


**Magnetometry measurements.** Magnetometry measurements were performed on 20 – 80 mg portions of powder contained in gelatin capsules, using a Quantum Design MPMS-5 SQUID magnetometer. Measurements as functions of temperature in the range  $5 \leq T \text{ (K)} \leq 300$  were carried out on warming in an applied magnetic field of 100 Oe after cooling in zero applied field (Zero-Field-Cooled (ZFC)) and subsequently after cooling in the measuring field (Field-Cooled (FC)).

## Results and Discussion

The samples prepared with compositions of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  appeared to be phase pure by laboratory PXRD and adopted the same structure, with comparable lattice parameters to those reported previously [5,6]. This suggests that the compounds are stoichiometric, and this was supported by our PND measurements (see below). Magnetometry measurements, were consistent with those previously reported [5,6]. The magnetic susceptibilities of both  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ , shown in Figure 2, exhibited broad maxima in the region 200 – 250 K. These broad susceptibility features are commonly found in low-dimensional antiferromagnetic systems in which

two-dimensional correlations resulting from strong intra-plane superexchange build and, on further cooling, long range three-dimensional magnetic ordering results from the effect of weaker inter-plane superexchange interactions [10,11,12]. The first derivative of the magnetic susceptibility (Figure 2 inset) revealed maxima at 190 K and 180 K for  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ . These maxima are assigned as the Néel temperatures ( $T_N$ ) for long-range three-dimensional magnetic ordering, and this is consistent with the temperature where magnetic Bragg peaks appear in the isostructural  $\text{Ba}_2\text{CoO}_2\text{Cu}_2\text{S}_2$  [4], and in measurements on several other two-dimensional systems [10,11,12].


Both compounds exhibit divergence of the ZFC and FC magnetic susceptibility curves at temperatures below the broad maxima, indicating history-dependent behaviour and possibly resulting from a minority disordered (i.e. spin-glass-like) component to the magnetism at low temperatures or due to a very slight spin canting. For  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  bifurcation occurs at  $\sim 160$  K, for  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  it occurs at the lower temperature of  $\sim 60$  K, below a second susceptibility maximum, of uncertain origin. Both Jin *et al.* [5] and Zhou *et al.* [6] note that this double maximum feature is also observed in  $\text{La}_2\text{CoO}_4$ , and in that case it arises from a spin-reorientation transition [13]. The variable temperature PND measurements of Smura *et al.* [4] did not show any evidence for any spin-reorientation transition in  $\text{Ba}_2\text{CoO}_2\text{Cu}_2\text{S}_2$  which also shows a double maximum in the susceptibility, so we presume that the behaviour is unrelated to that of  $\text{La}_2\text{CoO}_4$ . Curie and Weiss constants could not be extracted from the data on  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  because the measurements were not made at temperatures much higher than those of the antiferromagnetic transitions. A small feature in the magnetic susceptibility of  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  is also observed in the temperature range 45 – 50 K. This is not observed by Zhou *et al.* [6] so we ascribe it to a small amount of impurity below the level detectable by diffraction methods.

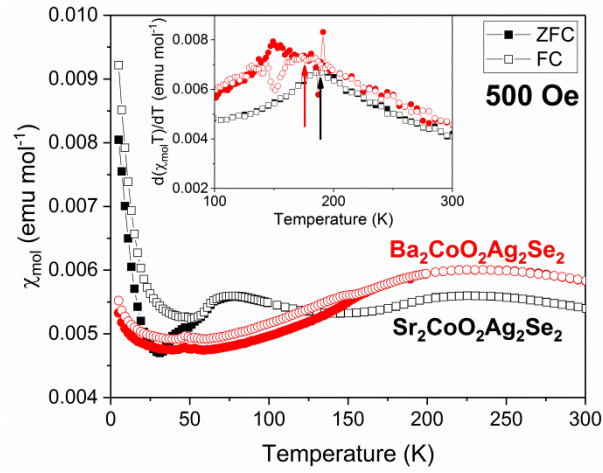

**Figure 2.** The ZFC and FC magnetic susceptibility of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ . The inset shows the first derivative  $d(\chi T)/dT$ , with arrows corresponding to the region that were identified as

$$T_N.$$

Refinement against the room temperature PND data confirmed the structural models previously found [5,6]. Previously we have shown that refinements against PND data from D2B and POLARIS are able to quantify non-stoichiometry that can occur in related compounds due to vacancies in the chalcogenide layer (i.e. Ag site vacancies in the present case) [4,14]. The refinements did not reveal any non-stoichiometry, consistent with the high purity of the samples obtained in stoichiometric reactions. The Rietveld plots are shown in Figure 3 and the refined parameters are shown in Table 1. Further databanks of the time-of-flight PND refinement of  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  may be found in the supporting information.

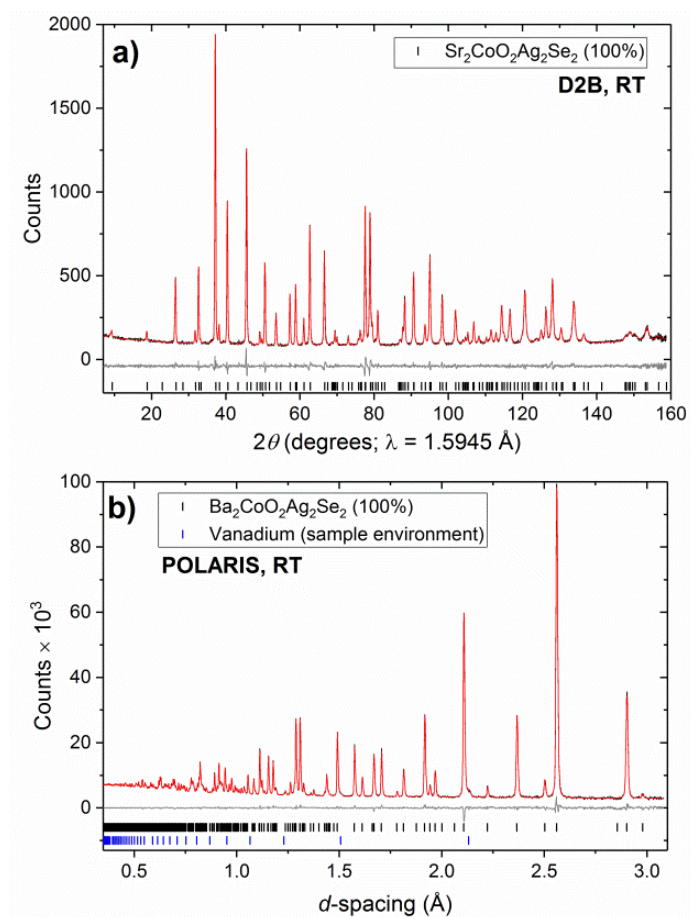

**Figure 3.** Rietveld refinements against powder neutron diffraction data collected for a)  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  using the fixed-wavelength diffractometer D2B (ILL) and b)  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  using the time-of-flight diffractometer POLARIS (ISIS).




**Table 1.** Rietveld refinement results against powder neutron diffraction data for Sr<sub>2</sub>CoO<sub>2</sub>Ag<sub>2</sub>Se<sub>2</sub> and Ba<sub>2</sub>CoO<sub>2</sub>Ag<sub>2</sub>Se<sub>2</sub>

Compound	Sr <sub>2</sub> CoO <sub>2</sub> Ag <sub>2</sub> Se <sub>2</sub>	Ba <sub>2</sub> CoO <sub>2</sub> Ag <sub>2</sub> Se <sub>2</sub>
Radiation	Neutron, constant wavelength	Neutron, time-of-flight
Instrument	D2B, ILL	POLARIS, ISIS
Temperature	298(2)	
Space group	I4/mmm	
<i>a</i> (Å)	4.10210(6)	4.21471(8)
<i>c</i> (Å)	19.4265(3)	20.0193(5)
Volume (Å <sup>3</sup> )	326.89(1)	355.62(2)
<i>z</i> (Sr/Ba)*	0.41682(7)	0.41233(4)
<i>z</i> (Se)*	0.15535(6)	0.16187(3)
<i>U</i> <sub>11</sub> (Sr/Ba) (Å <sup>2</sup> )	0.0036(5)	0.0012 (5)
<i>U</i> <sub>33</sub> (Sr/Ba) (Å <sup>2</sup> )	0.0094(8)	0.0043 (8)
<i>U</i> <sub>iso</sub> (Co) <sup>#</sup> (Å <sup>2</sup> )	0.004(1) <sup>#</sup>	0.0076(8)
<i>U</i> <sub>11</sub> (O) (Å <sup>2</sup> )	0.005(1)	0.0065(8)
<i>U</i> <sub>22</sub> (O) (Å <sup>2</sup> )	0.003(1)	0.014(1)
<i>U</i> <sub>33</sub> (O) (Å <sup>2</sup> )	0.010(1)	0.006(1)
<i>U</i> <sub>11</sub> (Ag) (Å <sup>2</sup> )	0.016(1)	0.0072(8)
<i>U</i> <sub>33</sub> (Ag) (Å <sup>2</sup> )	0.016(1)	0.017(1)
<i>U</i> <sub>11</sub> (Se) (Å <sup>2</sup> )	0.0055(5)	0.0077(4)
<i>U</i> <sub>33</sub> (Se) (Å <sup>2</sup> )	0.0072(7)	0.0067(5)
<i>R</i> <sub>wp</sub> (%)	4.378	4.002
*Sr/Ba, 4e(0,0,z); Co, 2a(0,0,0); O, 4c(0,½,0); Ag, 4d(0,½,¼); Se, 4e(0,0,z)		
<sup>#</sup> The Co atom was refined using an isotropic thermal displacement model		

PND data collected at 5 K revealed the presence of Bragg peaks that were not observed at room temperature. These Bragg peaks were found at long *d*-spacings and were indexed using a  $\sqrt{2}a \times \sqrt{2}a \times c$  expansion of the nuclear unit cell, suggesting that they resulted from long-range antiferromagnetic ordering.


The intensity of the magnetic peaks was modelled using the activation of magnetic symmetry modes, initially in the magnetic space group *P*1 (1.1). A good fit to the data could not be achieved using any single magnetic symmetry mode; therefore combinations of modes were considered. It was found that three different modes could be activated which resulted in intensity at the positions of the magnetic peaks without resulting in magnetic intensity elsewhere. These modes were mX2<sup>+</sup>(a), mX3<sup>+</sup>(a) and mX4<sup>+</sup>(a) and are shown in Figure S5. The best fit to the data was obtained for both Sr<sub>2</sub>CoO<sub>2</sub>Ag<sub>2</sub>Se<sub>2</sub> and Ba<sub>2</sub>CoO<sub>2</sub>Ag<sub>2</sub>Se<sub>2</sub> when the mX3<sup>+</sup>(a) and mX4<sup>+</sup>(a) modes were refined together. The combination of these two magnetic modes resulted in nearest-neighbour

antiferromagnetic interactions in the  $ab$ -plane, with no component in the  $c$ -axis, as shown in Figure 4.

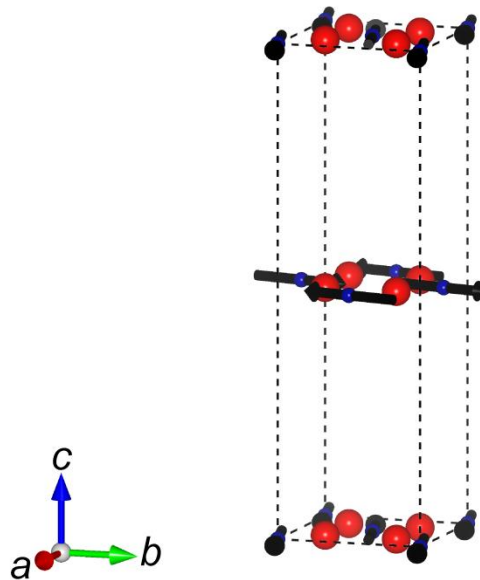

**Figure 4.** The magnetic structure of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ , for clarity only the cobalt (blue) and oxide (red) ions are shown.

Once the magnetic symmetry modes had been identified, the  $P_C4_2/n$  magnetic space group (86.72 in the Belov, Neronova and Smirnova (BNS) scheme; a setting of  $P_P4_2/m'$  (84.7.719) in the Opechowski and Guccione (OG) scheme) [15] was found to be the highest-symmetry magnetic space group that could accommodate the distortion of both these magnetic modes. The results are shown in the Rietveld plot in Figure 5 and Table 2. We note that in principle we cannot distinguish this model in which moments in adjacent planes are non-collinear from a model in which they are collinear [16] but the non-collinear model does enable retention of tetragonal symmetry.

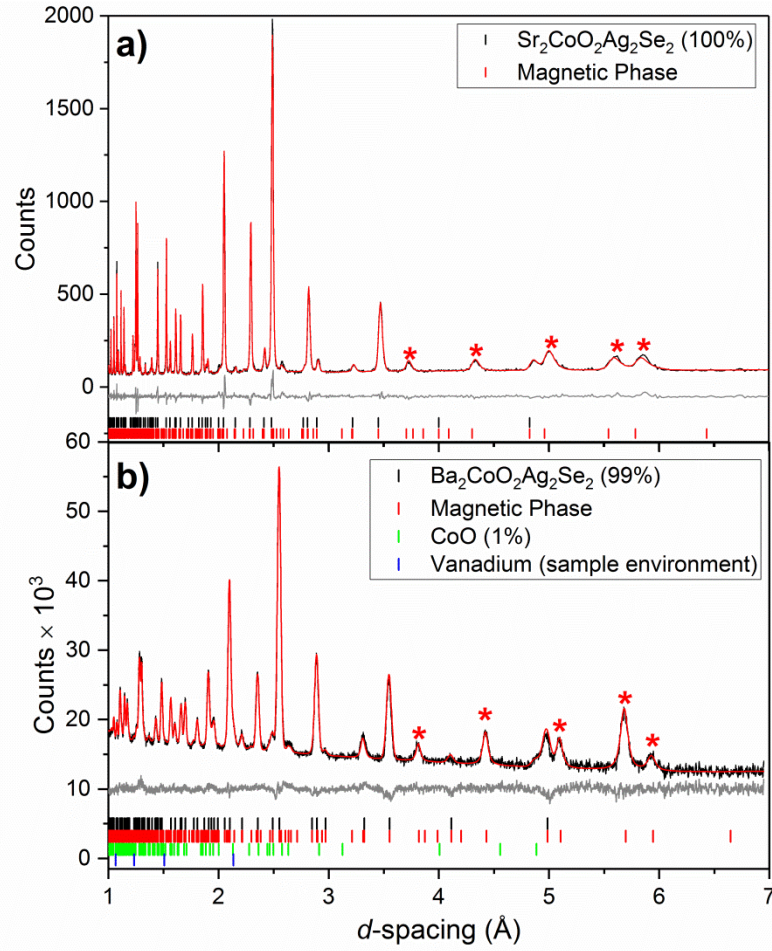


**Figure 5.** Rietveld plots of a)  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and b)  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  measured at 5 K using powder neutron diffraction.  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  was measured using the constant-wavelength diffractometer D2B (ILL), while  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  was measured on POLARIS (ISIS) (shown here is the A (35°) bank of the time-of-flight diffractometer). Both powder neutron diffraction patterns are shown plotted as functions of  $d$ -spacing for comparison.

**Table 2** Refined magnetic moments of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ , measured at 5 K, using powder neutron diffraction. The magnetic structure was modelled using a non-collinear (tetragonal) model as discussed in the main text.

Compound	$\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$	$\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$
Temperature (K)	5	
Magnetic space group	$P_4A_2/n$ (BNS scheme)	
$\mu_a$ ( $\mu_B$ )	0.7(1)	0.80(3)
$\mu_b$ ( $\mu_B$ )	3.7(1)	3.89(3)
$\mu_c$ ( $\mu_B$ )	0	0
$ \mu $ ( $\mu_B$ )	3.7(1)	3.97(3)

The magnetic structures of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  are similar to one another, the sole difference being a slightly larger magnitude of the ordered  $\text{Co}^{2+}$  moment in  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ . However, the magnitudes of the refined moments are within three standard deviations of one another.

It is known that high-spin  $d^7$   $\text{Co}^{2+}$  ions in an octahedral coordination carry an unquenched orbital contribution to the magnetic moment, resulting in ordered moments with a magnitude greater than the  $3 \mu_B$  expected if spin-only contributions are considered [17]. This is observed for CoO [18,19]. Reduction in the local Co symmetry from octahedral results in significant quenching of the orbital moment, but examination of a large number of oxide chalcogenide and oxide halide systems containing  $\text{Co}^{2+}$  revealed [4] that the orbital moment recovered as the distorted octahedral environment became increasingly distended, with the total ordered moment eventually exceeding that in CoO when the coordination environment approached square planar. This experimental observation was supported using a computational comparison of  $\text{Sr}_2\text{CoO}_2\text{Cu}_2\text{S}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Cu}_2\text{S}_2$  [4]. Figure. 6 shows a plot of ordered moment as a function of the ratio  $(\text{Co-X})/(\text{Co-O})$  where X is the axial anion O, chalcogenide or halide. Because of the increased sizes of the  $\text{Ag}^+$  cation and the  $\text{Se}^{2-}$  anion compared with the  $\text{Cu}^+$  cation and  $\text{S}^{2-}$  anion, the  $(\text{Co-X})/(\text{Co-O})$  ratio is smaller in  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  than in their counterparts with copper sulfide layers, as shown in Table 3. The ordered magnetic moments of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  are thus reduced in line with the trend, previously established by Smura *et al.* [4].

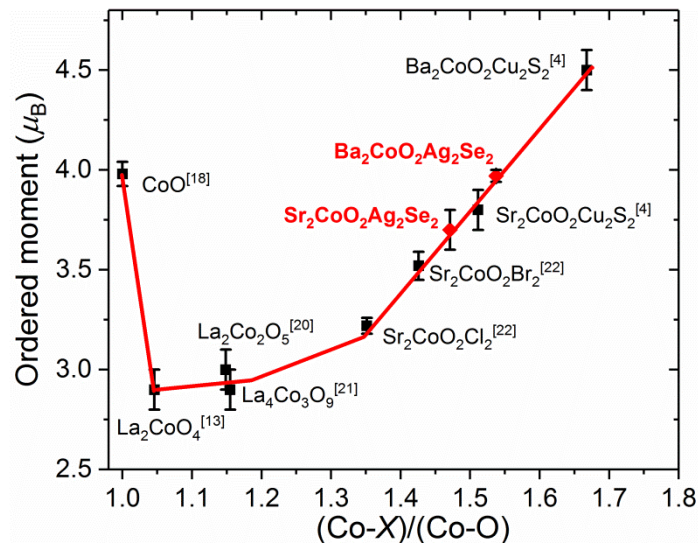

**Figure. 6.** Changing magnetic moment of  $\text{Co}^{2+}$  as a function of the coordination geometry from the literature (black) and from this work (red). Literature values are used for the bond lengths in the oxides [13,18,20,21], oxyhalides [22], and oxysulfides [4] with average values for the axial ( $\times 2$ ) and equatorial ( $\times 4$ ) Co–O bond lengths for systems with lower than  $D_{4h}$  symmetry at  $\text{Co}^{2+}$ . The line is a guide to the eye.

**Table 3.** Comparison of the bond distances and angles of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  with those of  $\text{Sr}_2\text{CoO}_2\text{Cu}_2\text{S}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Cu}_2\text{S}_2$  (data obtained from ref. [4]). All data was obtained from refinement against powder neutron diffraction data collected at room temperature.

Compound	$\text{Sr}_2\text{CoO}_2\text{Cu}_2\text{S}_2$ [4]	$\text{Ba}_2\text{CoO}_2\text{Cu}_2\text{S}_2$ [4]	$\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$	$\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$
$\text{Sr/Ba-O (Å)} \times 4$	2.5803(2)	2.7261(3)	2.6103(9)	2.7419(6)
$\text{Sr/Ba-Ch (Å)} \times 4$	3.1491(3)	3.2675(5)	3.2218(8)	3.3300(5)
$\text{Co-O (Å)} \times 4$	1.99565(1)	2.03210(2)	2.05105(3)	2.10736(4)
$\text{Co-Ch (Å)} \times 2$	3.0327(5)	3.3721(9)	3.0169(12)	3.2397(5)
$\text{Co-O/Co-Ch}$	1.5197(3)	1.6594(4)	1.4709(6)	1.5373(2)
$\text{Cu/Ag-Ch (Å)} \times 4$	2.4356(3)	2.4395(5)	2.7553(8)	2.7490(3)
$\text{Ch-Cu/Ag-Ch (°)} \times 4$	109.19(1)	107.82(2)	116.48(2)	114.351(9)
$\text{Ch-Cu/Ag-Ch (°)} \times 2$	110.04(2)	112.82(4)	96.22(4)	100.100(17)

## Conclusions

The magnetic structures of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  have been deduced and refined from powder neutron diffraction data. The long-range antiferromagnetic ordering of the localised  $\text{Co}^{2+}$  moments is consistent with the expectation of antiferromagnetic superexchange between like moments mediated by 180 degree superexchange via intervening oxide ions. The two compounds are shown to conform to a relationship for related compounds in which the magnitude of the large unquenched orbital contribution to the magnetic moment in the ordered phase is governed by the degree of distortion of the  $\text{CoO}_4\text{X}_2$  distended octahedral environment. Measurements on single crystals, including neutron spectroscopy, would be required to probe the subtleties evident in the susceptibility measurements in the magnetically ordered regime, and to determine the values of exchange constants.

## Acknowledgements

This work was supported by the UK EPSRC [grant numbers EP/M020517/1 and EP/P018874/1]. We thank the ISIS pulsed neutron and muon source and the Institut Laue Langevin for the award of neutron beam time. We thank the Diamond Light Source for studentship support for JNB. We are grateful to Dr. R I Smith for support on POLARIS and Dr E Suard for support on D2B.

## Competing Interests

The authors declare no competing interests.

## References

- 
- [1] W. J. Zhu, P. H. Hor, A. J. Jacobson, G. Crisci, T. A. Albright, S. H. Wang and T. Vogt,  $A_2Cu_2CoO_2S_2$  ( $A = Sr, Ba$ ), A Novel Example of a Square-Planar  $CoO_2$  Layer, *J. Am. Chem. Soc.*, 1997, **119**, 12398-12399.
- [2] E. Brechtel, G. Cordier and H. Schaefer, Oxidpnictides – Preparation and Crystal Structure of  $A_2Mn_3B_2O_2$  with  $A = Sr, Ba$  and  $B = As, Sb, Bi$ , *Z. Naturforsch., B: A Journal of Chemical Sciences*, 1979, **34B**, 777-780.
- [3] S. J. Clarke, P. Adamson, S. J. C. Herkelrath, O. J. Rutt, D. R. Parker, M. J. Pitcher and C. F. Smura, Structures, Physical Properties, and Chemistry of Layered Oxychalcogenides and Oxypnictides, *Inorg. Chem.*, 2008, **47**, 8473-8486.
- [4] C. F. Smura, D. R. Parker, M. Zbiri, M. R. Johnson, Z. A. Gál and S. J. Clarke, High-Spin Cobalt(II) Ions in Square Planar Coordination: Structures and Magnetism of the Oxysulfides  $Sr_2CoO_2Cu_2S_2$  and  $Ba_2CoO_2Cu_2S_2$  and Their Solid Solution, *J. Am. Chem. Soc.*, 2011, **133**, 2691-2705.
- [5] S. Jin, X. Chen, J. Guo, M. Lei, J. Lin, J. Xi, W. Wang and W. Wang,  $Sr_2Mn_3Sb_2O_2$  Type Oxyselenides: Structures, Magnetism, and Electronic Properties of  $Sr_2AO_2M_2Se_2$  ( $A = Co, Mn$ ;  $M = Cu, Ag$ ), *Inorg. Chem.*, 2012, **51**, 10185-10192.
- [6] T. Zhou, Y. Wang, S. Jin, D. Li, X. Lai, T. Ying, H. Zhang, S. Shen, W. Wang and X. Chen, Structures and Physical Properties of Layered Oxyselenides  $Ba_2MO_2Ag_2Se_2$  ( $M = Co, Mn$ ), *Inorg. Chem.*, 2014, **53**, 4154-4160.
- [7] S. Hull, R. I. Smith, W. I. F. David, A. C. Hannon, J. Mayers and R. Cywinski, The Polaris powder diffractometer at ISIS, *Physica B: Condensed Matter*, 1992, **180-181**, 1000-1002.
- [8] A. A. Coelho, *TOPAS Academic Version 5*, Coelho Software, Brisbane, Australia, 2012.
- [9] B. J. Campbell, H. T. Stokes, D. E. Tanner, D. M. Hatch, ISODISPLACE: a web-based tool for exploring structural distortions. *J. Appl. Crystallogr.*, 2006, **39**, 607-614; *ISODISTORT: ISOTROPY Software Suite*, *iso.byu.edu*.
- [10] C. S. Knee, D. J. Price, M. R. Lees and M. T. Weller, Two- and three-dimensional magnetic order in the layered cobalt oxychloride  $Sr_2CoO_3Cl$ , *Phys. Rev. B*, 2003, **68**, 174407.
- [11] J. B. He, D. M. Wang, H. L. Shi, H. X. Yang, J. Q. Li and G. F. Chen, Synthesis, structure and magnetic properties of the layered iron oxychalcogenide  $Na_2Fe_2Se_2O$ , *Phys. Rev. B* 2011, **84**, 205212.
- [12] N. Ni, E. Climent-Pascual, S. Jia, Q. Huang and R. J. Cava, Physical properties and magnetic structure of the layered oxyselenide  $La_2O_3Mn_2Se_2$ , *Phys. Rev. B*, 2010, **82**, 214419.

- 
- [13] K. Yamada, M. Matsuda, Y. Endoh, B. Keimer, R. J. Birgeneau, S. Onodera, J. Mizusaki, T. Matsuura and G. Shirane, Successive antiferromagnetic phase transitions in single-crystal  $\text{La}_2\text{CoO}_4$ , *Phys. Rev. B*, 1989, **39**, 2336-2343.
- [14] M. J. Pitcher, C. F. Smura, and S. J. Clarke, Stoichiometric  $\text{CeOCuS}$  – a well-behaved Ce(III) layered oxysulfide, *Inorg. Chem.* 2009, **48**, 9054-9056.
- [15] D. B. Litvin, *Magnetic Group Tables: 1-, 2- and 3-Dimensional Magnetic Subperiodic Groups and Magnetic Space Groups*, International Union of Crystallography **2013**; ISBN 978-0-9553602-2-0 doi:10.1107/9780955360220001.
- [16] G. Shirane, A note on the magnetic intensities of powder neutron diffraction, *Acta Crystallogr.*, 1959, **12**, 282-285.
- [17] B. N. Figgis and M. A. Hitchman, *Ligand Field Theory and Its Applications*, Wiley, New York, 2000.
- [18] W. Jauch, M. Reehuis, H. J. Bleif, F. Kubanek and P. Pattison, Crystallographic symmetry and magnetic structure of  $\text{CoO}$ , *Phys. Rev. B*, 2001, **64**, 052102.
- [19] W. Jauch and M. Reehuis, Electron density distribution in paramagnetic and antiferromagnetic  $\text{CoO}$ : A  $\gamma$ -ray diffraction study, *Phys. Rev. B*, 2002, **65**, 125111.
- [20] O. H. Hansteen, H. Fjellvåg and B. C. Hauback, Crystal Structure and Magnetic Properties of  $\text{La}_2\text{Co}_2\text{O}_5$ , *J. Solid State Chem.*, 1998, **141**, 411-417.
- [21] O. H. Hansteen, H. Fjellvåg and B. C. Hauback, Crystal structure, thermal and magnetic properties of  $\text{La}_4\text{Co}_3\text{O}_9$ . Phase relations for  $\text{La}_4\text{Co}_3\text{O}_{10-\delta}$  ( $0.00 \leq \delta \leq 1.00$ ) at 673 K, *J. Mater. Chem.*, 1998, **8**, 2089-2093.
- [22] C. S. Knee and M. T. Weller, Neutron diffraction study of crystal structure and antiferromagnetic order in  $\text{Sr}_2\text{CoO}_2\text{X}_2$  ( $\text{X} = \text{Cl}, \text{Br}$ ), *Phys. Rev. B*, 2004, **70**, 144406.

# Magnetic ordering in the layered oxyselenides $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ and $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$

---

Sebastian J. C. Herkelrath<sup>a</sup>, Jack N. Blandy<sup>a,b</sup>, and Simon J. Clarke<sup>a,\*</sup>

<sup>a</sup>*Department of Chemistry, University of Oxford, Inorganic Chemistry Laboratory, South Parks Road, Oxford OX1 3QR, United Kingdom.*


<sup>b</sup>*Diamond Light Source Ltd., Harwell Science and Innovation Campus, Didcot OX11 0DE, United Kingdom.*

## 1. Supporting Information


Table of contents
Rietveld plots of $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ measured at RT using POLARIS (A and E banks)
Plot comparing the powder neutron diffraction pattern of $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ at RT and 5 K
Plot comparing the powder neutron diffraction pattern of $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ at RT and 5 K
Diagram showing possible magnetic modes
Rietveld plot of $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ measured at 5 K, shown as a function of $2\theta$
Rietveld plots of $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ measured at 5 K using POLARIS (C and E banks)

email address: [simon.clarke@chem.ox.ac.uk](mailto:simon.clarke@chem.ox.ac.uk)




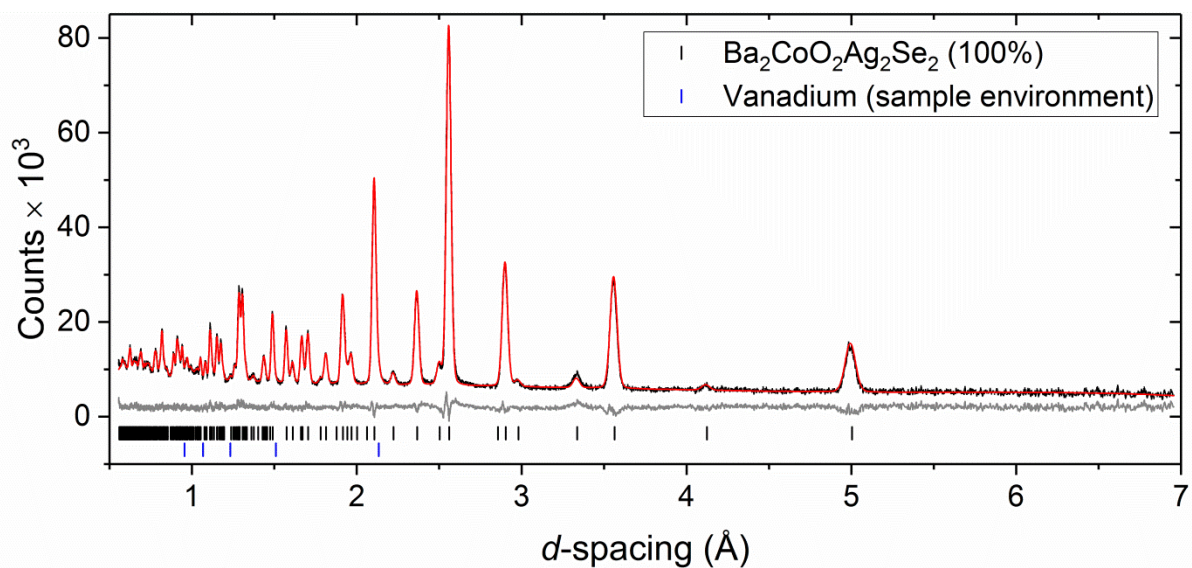


**Figure S1.** Rietveld refinement against the powder neutron diffraction pattern of  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ , measured at room temperature using the A bank ( $35^\circ$ ) of POLARIS (ISIS)

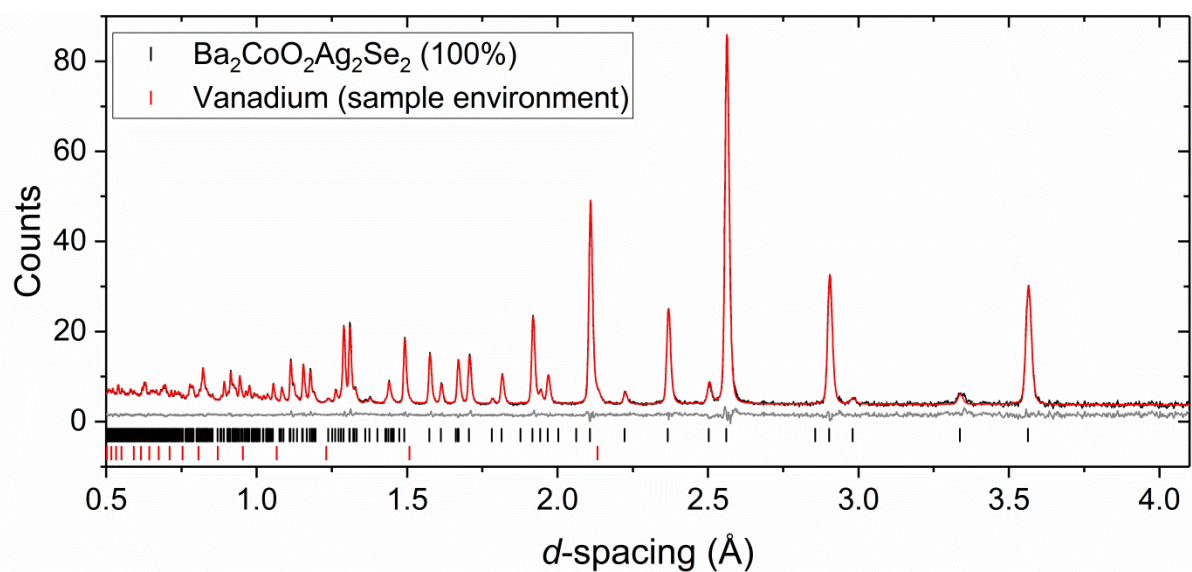


**Figure S2.** Rietveld refinement against the powder neutron diffraction pattern of  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ , measured at room temperature using the E bank ( $90^\circ$ ) of POLARIS (ISIS)

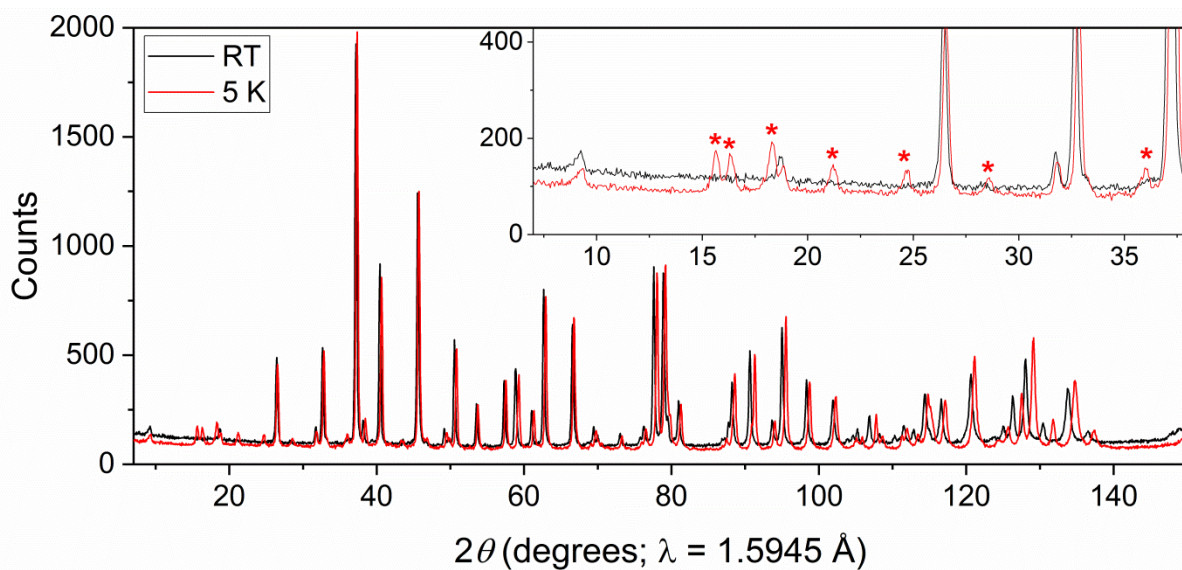


**Figure S3.** Comparison of the powder neutron diffraction pattern of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ , measured at room temperature (RT) and 5 K. \* symbols indicate the highest intensity peaks that were identified as magnetic. The powder neutron diffraction patterns were measured using D2B (ILL)

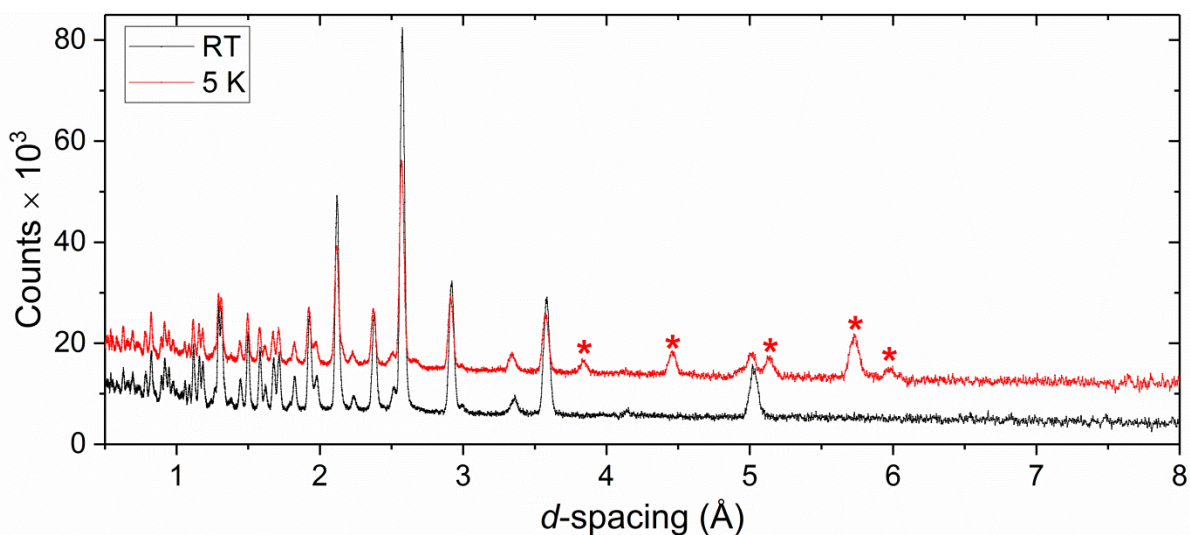


**Figure S4.** Comparison of the powder neutron diffraction pattern of  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$ , measured at room temperature (RT) and 5 K. \* symbols indicate the highest intensity peaks that were identified as magnetic. The powder neutron diffraction patterns were measured using POLARIS (ISIS)

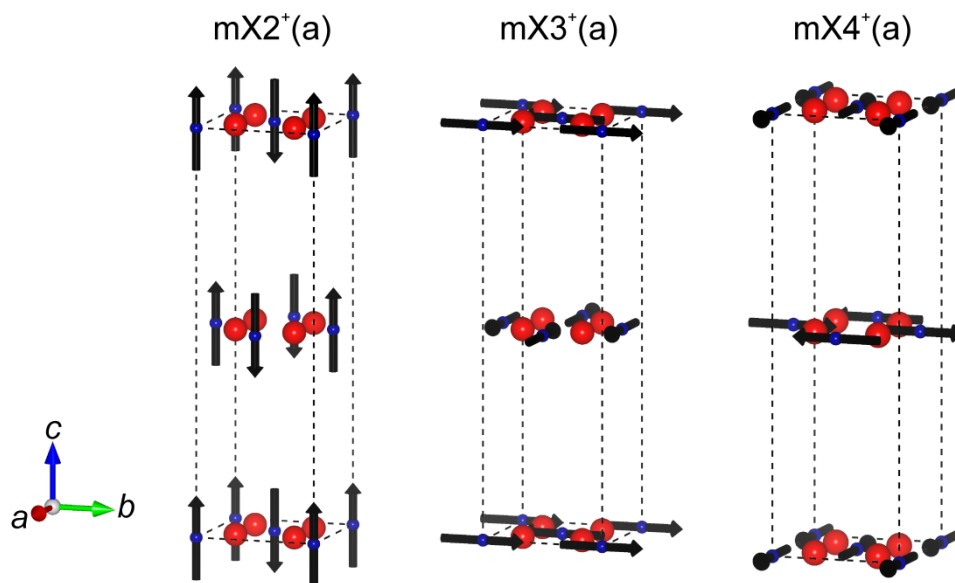


**Figure S5.** Magnetic symmetry modes considered when analysing the magnetic structures of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  and  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$

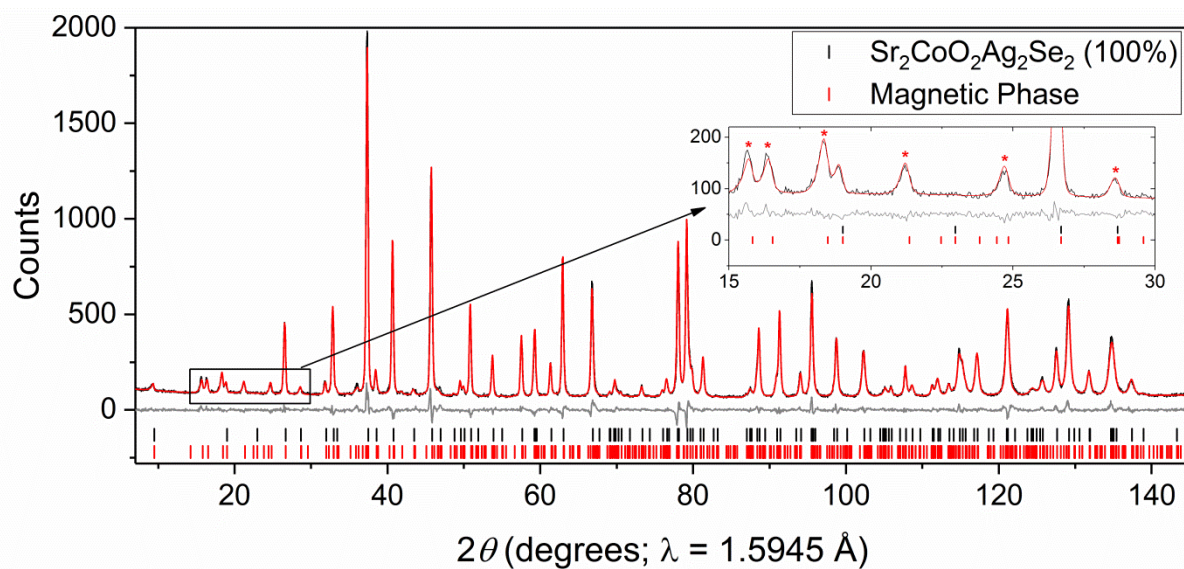

**Figure S6.** Rietveld refinement against the powder neutron diffraction pattern of  $\text{Sr}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  measured at 5 K on the constant-wavelength diffractometer D2B (ILL). The main magnetic peaks in the inset are emphasised by \* symbols.

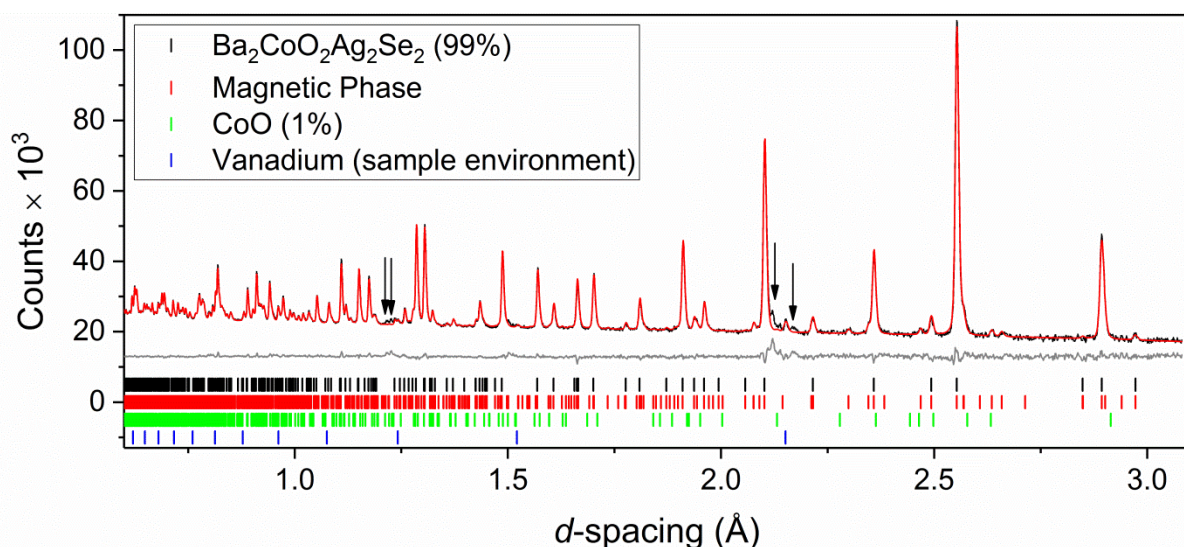

**Figure S7.** Rietveld refinement against the powder neutron diffraction data of  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  measured at 5 K using the C bank ( $145^\circ$ ) of the time-of-flight neutron diffractometer POLARIS (ISIS). Arrows indicate sample environment peaks arising from the vanadium walls of the cryostat.

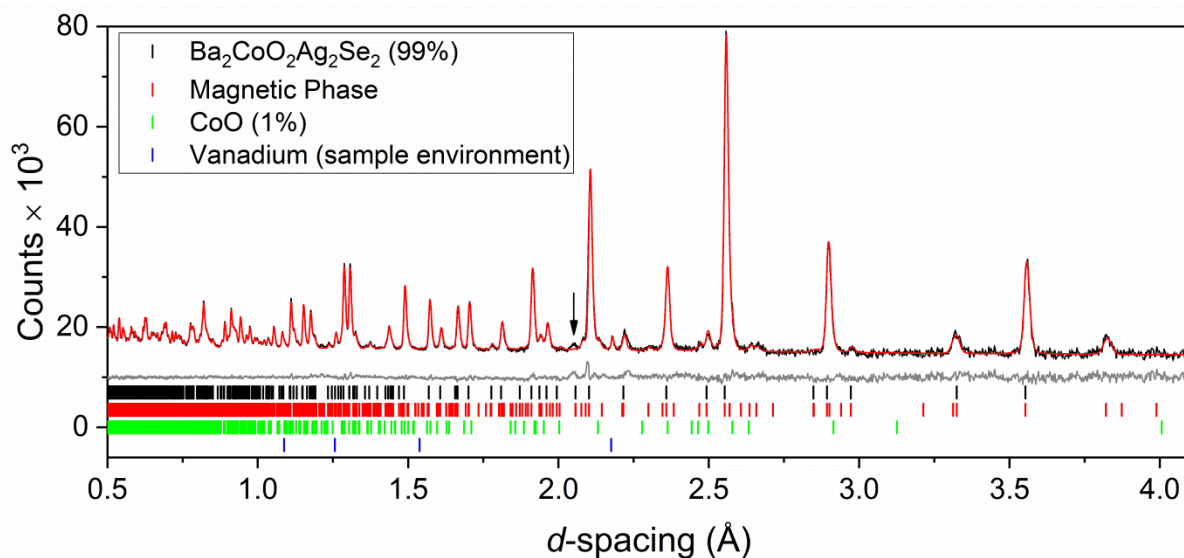

**Figure S8.** Rietveld refinement against the powder neutron diffraction data of  $\text{Ba}_2\text{CoO}_2\text{Ag}_2\text{Se}_2$  measured at 5 K using the E bank ( $90^\circ$ ) of the time-of-flight neutron diffractometer POLARIS (ISIS). The arrow indicates an unindexed peak that does not appear at the corresponding position in the  $145^\circ$  bank and is therefore assumed to arise from the sample environment.